

AD 787 274

AD-787 274

SURVEY AND CRITICAL REVIEW OF  
DYNAMIC MECHANICAL PROPERTIES OF METALS

WATERVLIET ARSENAL

JULY 1974

DISTRIBUTED BY:

**NTIS**

National Technical Information Service  
U. S. DEPARTMENT OF COMMERCE

ADDITIONAL BY	
HTG	<input checked="" type="checkbox"/>
BCC	<input type="checkbox"/>
UNAPPROVED	<input type="checkbox"/>
JUSTIFICATION	
BY	
EXTENSION/AVAILABILITY CODES	
CLASS	AVAIL. OF SPECIAL
A	

# DISPOSITION

Destroy this report when it is no longer needed. Do not return it to the originator.

# DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

UNCLASSIFIED  
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER NVT-TR-74084	2. JOINT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER AD-787 274
4. TITLE (and Subtitle) SURVEY AND CRITICAL REVIEW OF DYNAMIC MECHANICAL PROPERTIES OF METALS		5. TYPE OF REPORT & PERIOD COVERED
7. AUTHOR(s) D. P. Kendall		6. PERFORMING ORG. REPORT NUMBER
8. PERFORMING ORGANIZATION NAME AND ADDRESS Benet Weapons Laboratory Watervliet Arsenal, Watervliet, N.Y. 12189 SARW-RDT		9. CONTRACT OR GRANT NUMBER(s)
11. CONTROLLING OFFICE NAME AND ADDRESS U.S. Army Armament Command Rock Island, Illinois 61201		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS AMMS No. 552D.11.80700 DA Proj. No. 1J562604A607
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE July 1974
		13. NUMBER OF PAGES 54
		15. SECURITY CLASS. (of this report) Unclassified
16. DISTRIBUTION STATEMENT (of this Report)  Approved for public release; distribution unlimited.		18. DECLASSIFICATION/DOWNGRADING SCHEDULE
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Strain Rate Dynamic Properties Mechanical Properties Metals Temperature Effects		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The general technical literature from all known sources that contains mechanical property data on metals at strain rates in the range of $10^{-2}$ to $10^{-4}$ sec $^{-1}$ is reviewed. The general trends of the data are discussed for each metal and alloy class. Results on the same material from different sources are compared and consensus results given where possible. The effects of elevated and low temperatures are discussed.		

SEE REVERSE SIDE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Block No. 20

Abstract continued

Information is also presented in the form of charts which show the range of strain rate and temperature for which data are available for each metal and alloy class.

//

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

WVT-TR-74034

AD

SURVEY AND CRITICAL REVIEW OF  
DYNAMIC MECHANICAL PROPERTIES OF METALS

DAVID P. KENDALL



**BENET WEAPONS LABORATORY**  
**WATERVLIET ARSENAL**  
**WATERVLIET, N.Y. 12189**

JULY 1974

**TECHNICAL REPORT**

AMCMS No. 52D.11.80700

DA Project No. 1J562604A607

APPROVED FOR PUBLIC RELEASE DISTRIBUTION UNLIMITED

## TABLE OF CONTENTS

	Page
ACKNOWLEDGMENTS	ii
INTRODUCTION	1
IRON BASE MATERIALS	4
ALUMINUM BASE MATERIALS	19
MAGNESIUM ALLOYS	27
TITANIUM ALLOYS	29
COPPER	35
LEAD	35
NICKEL AND NICKEL BASE ALLOYS	37
REFRACTORY METALS	39
OTHER METALS AND ALLOYS	42
REFERENCES	45

#### ACKNOWLEDGMENTS

Appreciation is expressed to the U. S. Army Small Arms Systems Agency for providing financial support for this work and to Dr. S. C. Chou of AMMRC, Watertown for suggesting the method of data presentation and for assistance in locating references.

## INTRODUCTION

The purpose of this report is to provide the designer or the materials engineer with a general review of what is currently known about the effects of high rates of loading on the strength of metals and alloys. The information is presented in the form of charts which show the strain rate and temperature regions in which data are available for each of the 18 metals or alloy classes considered. References to the source of the data are shown on the charts.

Along with each chart is a narrative discussion of the general trends of the data for the material considered. The intent of this discussion is not to provide actual design data or to completely summarize the results available. It is only to present general trends and areas of agreement or disagreement among the various references. Since data on the dynamic behavior of materials can be obtained in a number of different ways and under greatly varying conditions it is the opinion of the author that presentation of design data in a summary report of this type can be misleading and dangerous. To include all of the conditions which may affect the usefulness of the data referenced for design purposes would be prohibitively time consuming and would serve no real purpose. The best source of any data which will be used for actual design purposes is the original work in which the data was published.

An important consideration in using any of the data referenced in this report is the fact that the strain rate sensitivity of any material



can be greatly affected by heat treatment, microstructure and cold working. As an example of this, the strain rate sensitivity of a 4340 alloy steel in the quenched and tempered condition can be significantly affected by whether the microstructure is 100 percent martensite or a mixture of martensite and bainite. Therefore, in using any of these data in a critical design application the designer must be sure that the material used in his structure is the same as that used to obtain the test data.

The list of references used for this survey is believed to be as complete as possible in view of the limited time and funds available. However, there are undoubtedly a number of publications that should have been included and were overlooked. If any reader is aware of such publications the author would appreciate hearing of them since the intention is to update this report at some later date.

Papers or reports of a primarily theoretical nature that contain little or no original experimental data have been intentionally omitted from this review. It is not the intent of this work to review all of the many theoretical approaches to the understanding of materials at high rates of strain. This is not intended to diminish the importance of such work but it is not considered as being within the scope of this review.

In order to facilitate the addition of references as they become available, the list of references for this survey are arranged according to the first letter of the last name of the first named author. They are identified by this letter followed by a number which originally represented the alphabetical order of the authors. However, as references

were added, no attempt was made to maintain an alphabetical order within a group of references of the same code letter.

In addition to the references used in the discussion of the individual materials, there are several good surveys on high strain rate behavior of metals that have been previously published. Most of the information contained in these surveys has been considered in arriving at the general conclusions given in this report.

The most complete and current surveys are references E1, G7 and L2. Reference G7 contains a very complete review on steels and considers low, intermediate and high strength steels. Reference L2 covers all materials but most of the results given are for pure metals, aluminum alloys and mild steels. Reference E1 considers the combined effect of strain rate and temperature on an extremely wide variety of materials and presents rather complete summaries of the data from all of the references used.


## IRON BASED MATERIALS

### High Purity and Low Carbon Iron ( $<0.03\%C$ )

Room temperature results are available for high purity iron, "Armco" and Ferrovac E" irons and a special 0.15% Ti alloy for strain rates ranging from  $10^{-4}$  to  $2 \times 10^3 \text{ sec}^{-1}$ . The results are all quite similar showing a linear increase in strength with logarithmic strain rate up to about  $10 \text{ sec}^{-1}$ . The yield strength increases from about 10 ksi to 30 ksi over this range. At higher rates a more rapid increase is found. The flow stress at various strain values follows the same trend as the yield strength except for the annealed high purity iron at large strains (10-15%). For the latter case this material is rate independent up to a strain rate of  $1 \text{ sec}^{-1}$  and strongly rate sensitive at higher rates.

Results are also available at low temperatures to  $-195^\circ\text{C}$ . With decreasing temperature the strength increases considerably while the rate sensitivity decreases. At  $-195^\circ\text{C}$  the "static" yield strength is about 100 ksi and increases to 120 ksi at a strain rate of  $10 \text{ sec}^{-1}$ . At elevated temperatures the only available results are for Ferrovac E in the very high strain rate region ( $0.2 \times 10^3$  to  $6 \times 10^3 \text{ sec}^{-1}$ ). Above  $1.5 \times 10^3 \text{ sec}^{-1}$  a linear relationship between flow stress and strain rate is found. Elevated temperatures up to  $500^\circ\text{C}$  ( $930^\circ\text{F}$ ) result in a decrease in the slope of this relationship so that the relative strength increase for a strain rate increase from  $1.5 \times 10^3 \text{ sec}^{-1}$  remains essentially constant.

Special conditions studied are effects of neutron irradiation (C4) and of hydrostatic pressure (R1) and strain rate change effects (S5).

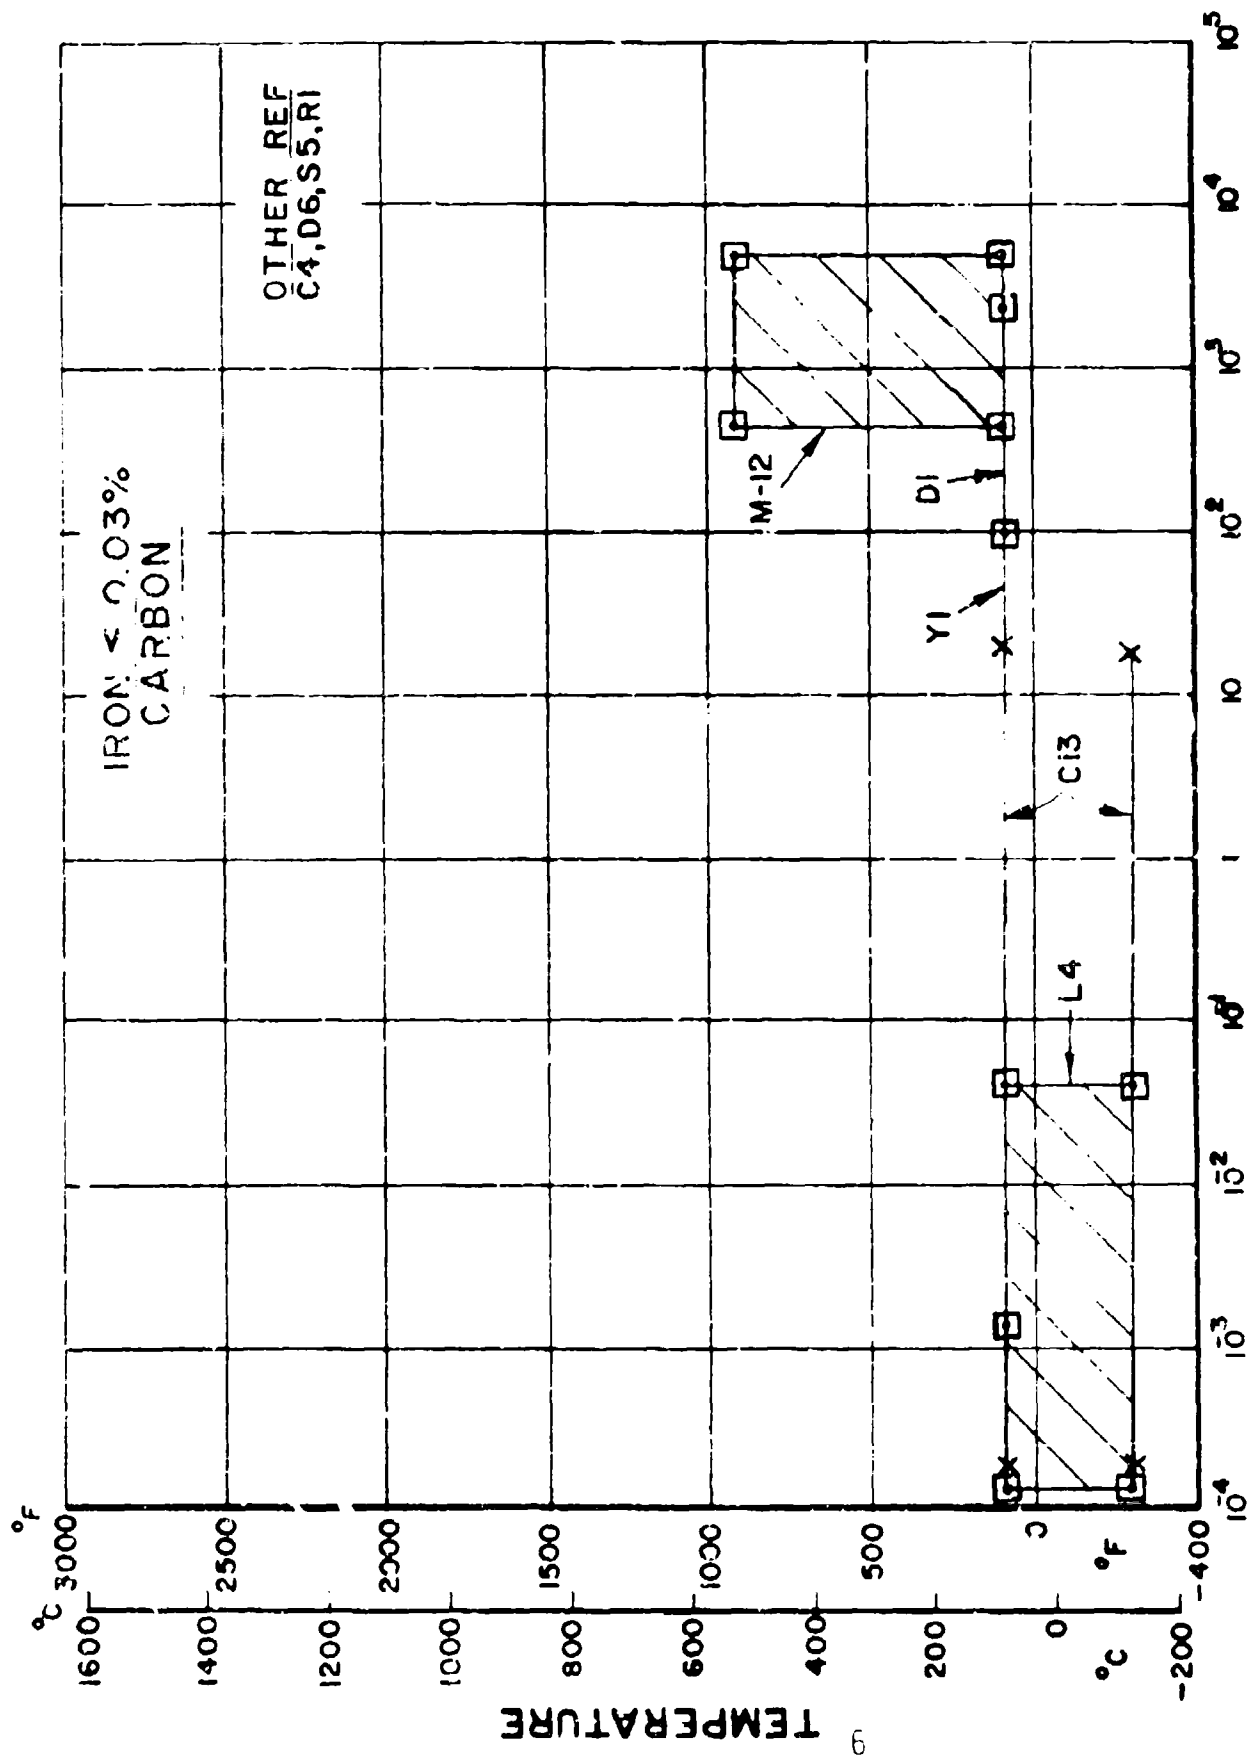

### Plain Carbon Steels ( $>0.03\%C$ )

There are over 14 references containing data on this material at room temperature. All of these show this material to be highly rate sensitive at room temperature in the annealed condition. Since this class of materials shows a distinct yield point instability phenomenon, it exhibits both an upper and lower yield strength. It also exhibits a delayed yield phenomenon which causes the upper yield strength to be more rate sensitive than the lower yield strength. The lower yield strength is a linear function of logarithmic strain rate from about  $10^{-2}$  to  $10^3 \text{ sec}^{-1}$ . A 100% increase in strength is generally found over this range. At strain rates below  $10^{-2}$  this material is essentially rate insensitive. Above about  $5 \times 10^3$  a significant increase in rate sensitivity to a linear relationship is reported. The upper yield strength is a power law function of strain rate for values exceeding  $10^{-3}$ . A 100% increase is found at a strain rate of about  $10 \text{ sec}^{-1}$ . The upper limit of this power law relationship is not known due to the experimental difficulties in measuring the upper yield strength at very high rates. Results for flow stress at various strain values follow the same trends as the lower yield strength but with decreasing rate sensitivity at higher strain values.


The effects of elevated and low temperatures on the rate sensitivity of this material have been studied quite extensively

by several investigators. The effect of increasing temperature is to slightly increase the slope of the yield stress-strain rate curve (on a log-log basis). However, the strain rate dividing the rate sensitive and insensitive regions is significantly increased. Increasing the temperature to 600F (590K) increases this transition strain rate by 3 orders of magnitude. For certain combinations of material, temperature and strain the flow stress may show a negative rate sensitivity (decreasing flow stress with increasing strain rate) in the intermediate strain rate range.

The effects of decreasing temperature are opposite to those given above for increasing temperature.

Most of the available results are for annealed material. Work hardening decreases the rate sensitivity in the intermediate strain rate region, and increases the strain rate dividing the rate sensitive and insensitive regions. Elevated temperature may result in a slight negative rate sensitivity for cold worked steels.

Other conditions considered are grain size effects (K5), biaxial loading (L1) and delay time effects (R4).

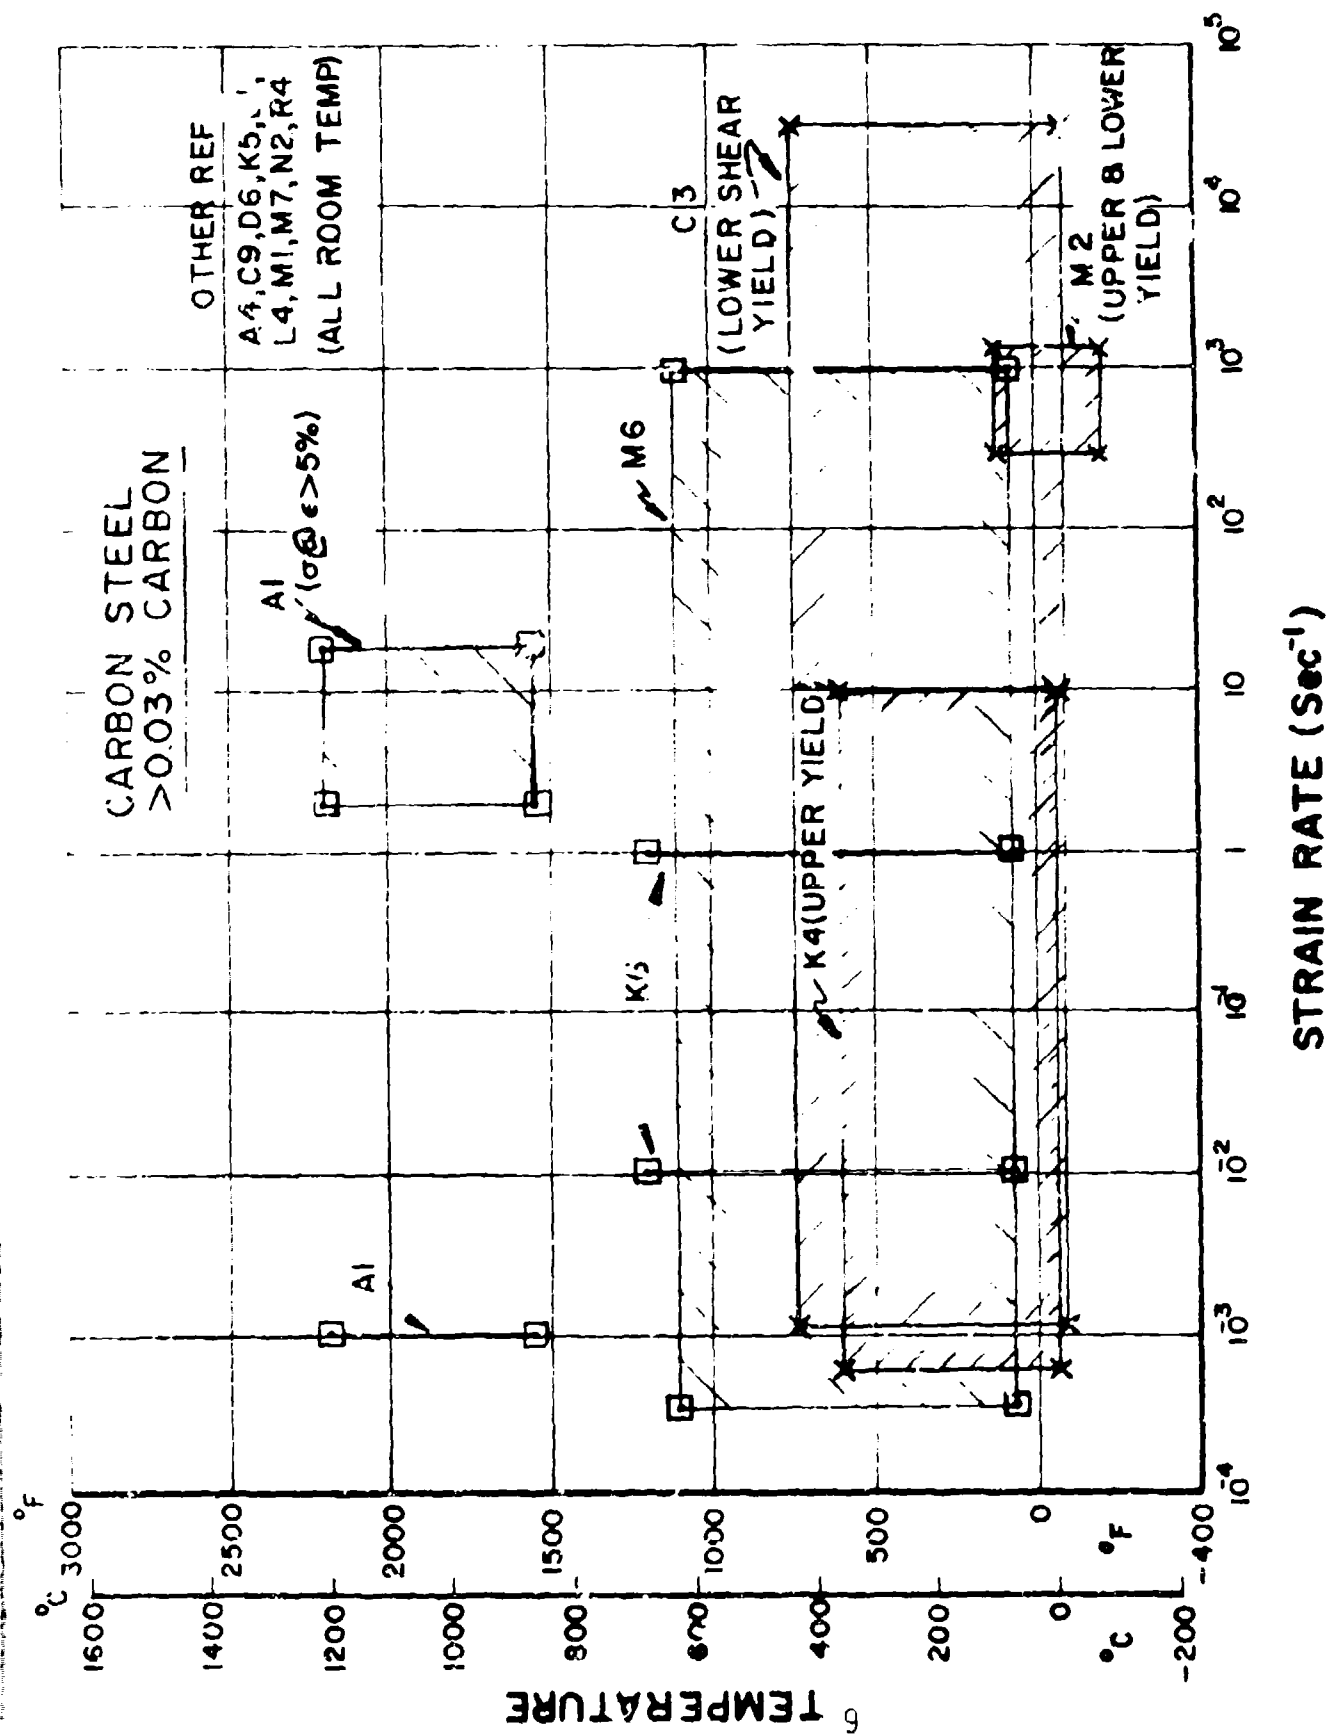




### Low Alloy Steels (4340 And Similar)


This class of materials generally shows very little strain rate sensitivity both at room temperature and at elevated temperatures in their range of usable operating temperature. However, they do exhibit a region of rate sensitivity at strain rates exceeding some transition rate which ranges from 1.0 to 100  $\text{sec}^{-1}$  depending on alloy content, heat treatment and grain size. Fine grained martensitic material shows the highest value of this transition strain rate. Course grained martensite and bainite have progressively lower transition rates. The effect of elevated temperature is to shift this transition rate to higher values, as with mild steels.

At temperatures in the hot working range (900 to 1200C) the flow stress at strain values ranging from 5 to 70% increases significantly with strain rate. These increases range from 50 to 100% for a strain rate of 100  $\text{sec}^{-1}$  over that for 1.5  $\text{sec}^{-1}$ .

At static strain rates, most alloy steels exhibit a sharp "knee" in the yield strength-temperature curve with the strength decreasing very rapidly with temperatures above this point. The temperature associated with this "knee" ranges from about 800 to 1200 F depending on alloy content. At a temperature just below this "knee" an inverse strain rate sensitivity has been found for several alloys. This can result in a decrease in strength of as much as 20% at a strain rate of about 10  $\text{sec}^{-1}$ . This can be attributed to strain aging


effects or to a general class of metallurgical phenomena referred to as structural deformational instability. This will be further discussed under aluminum alloys.

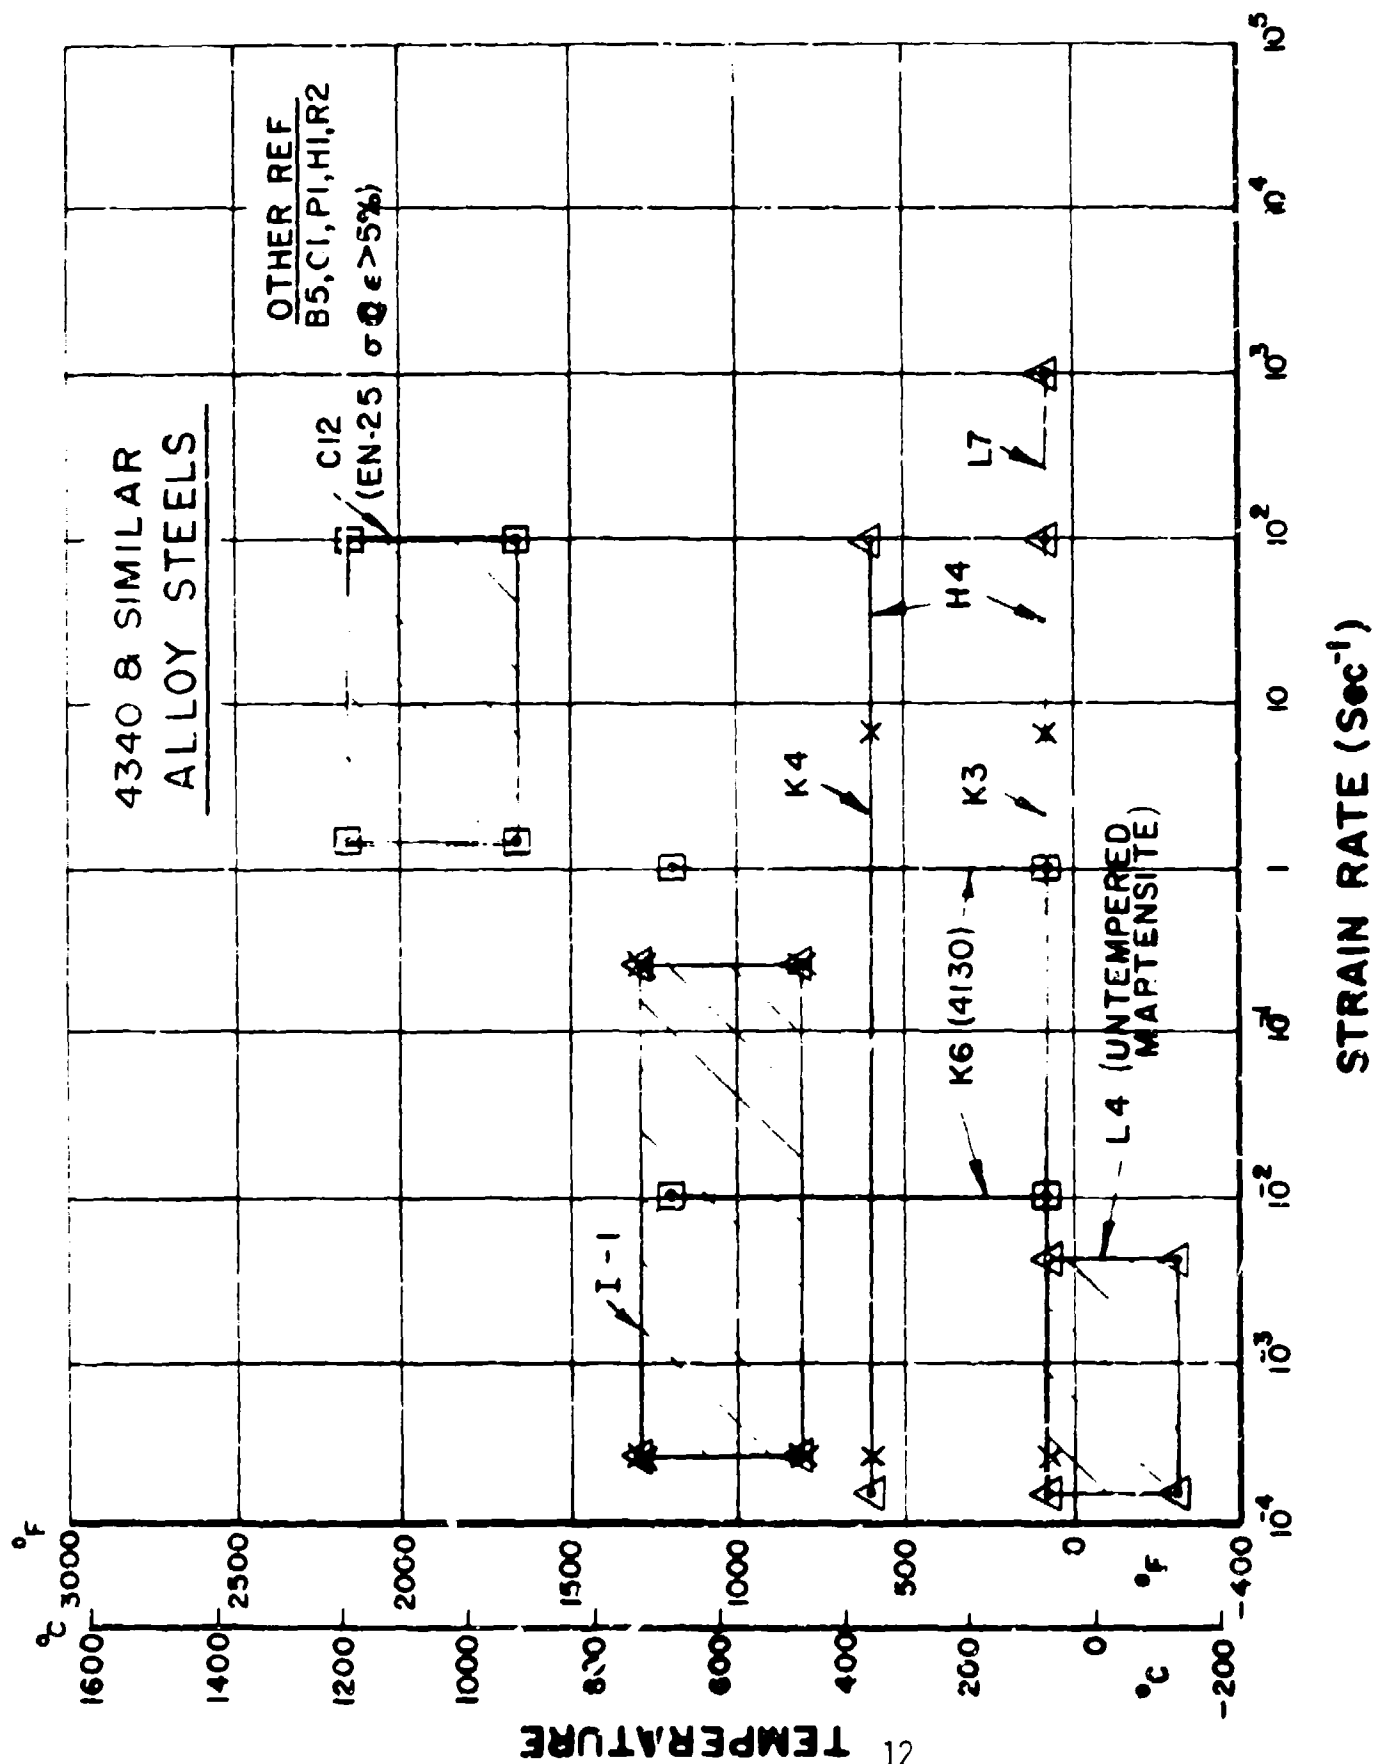

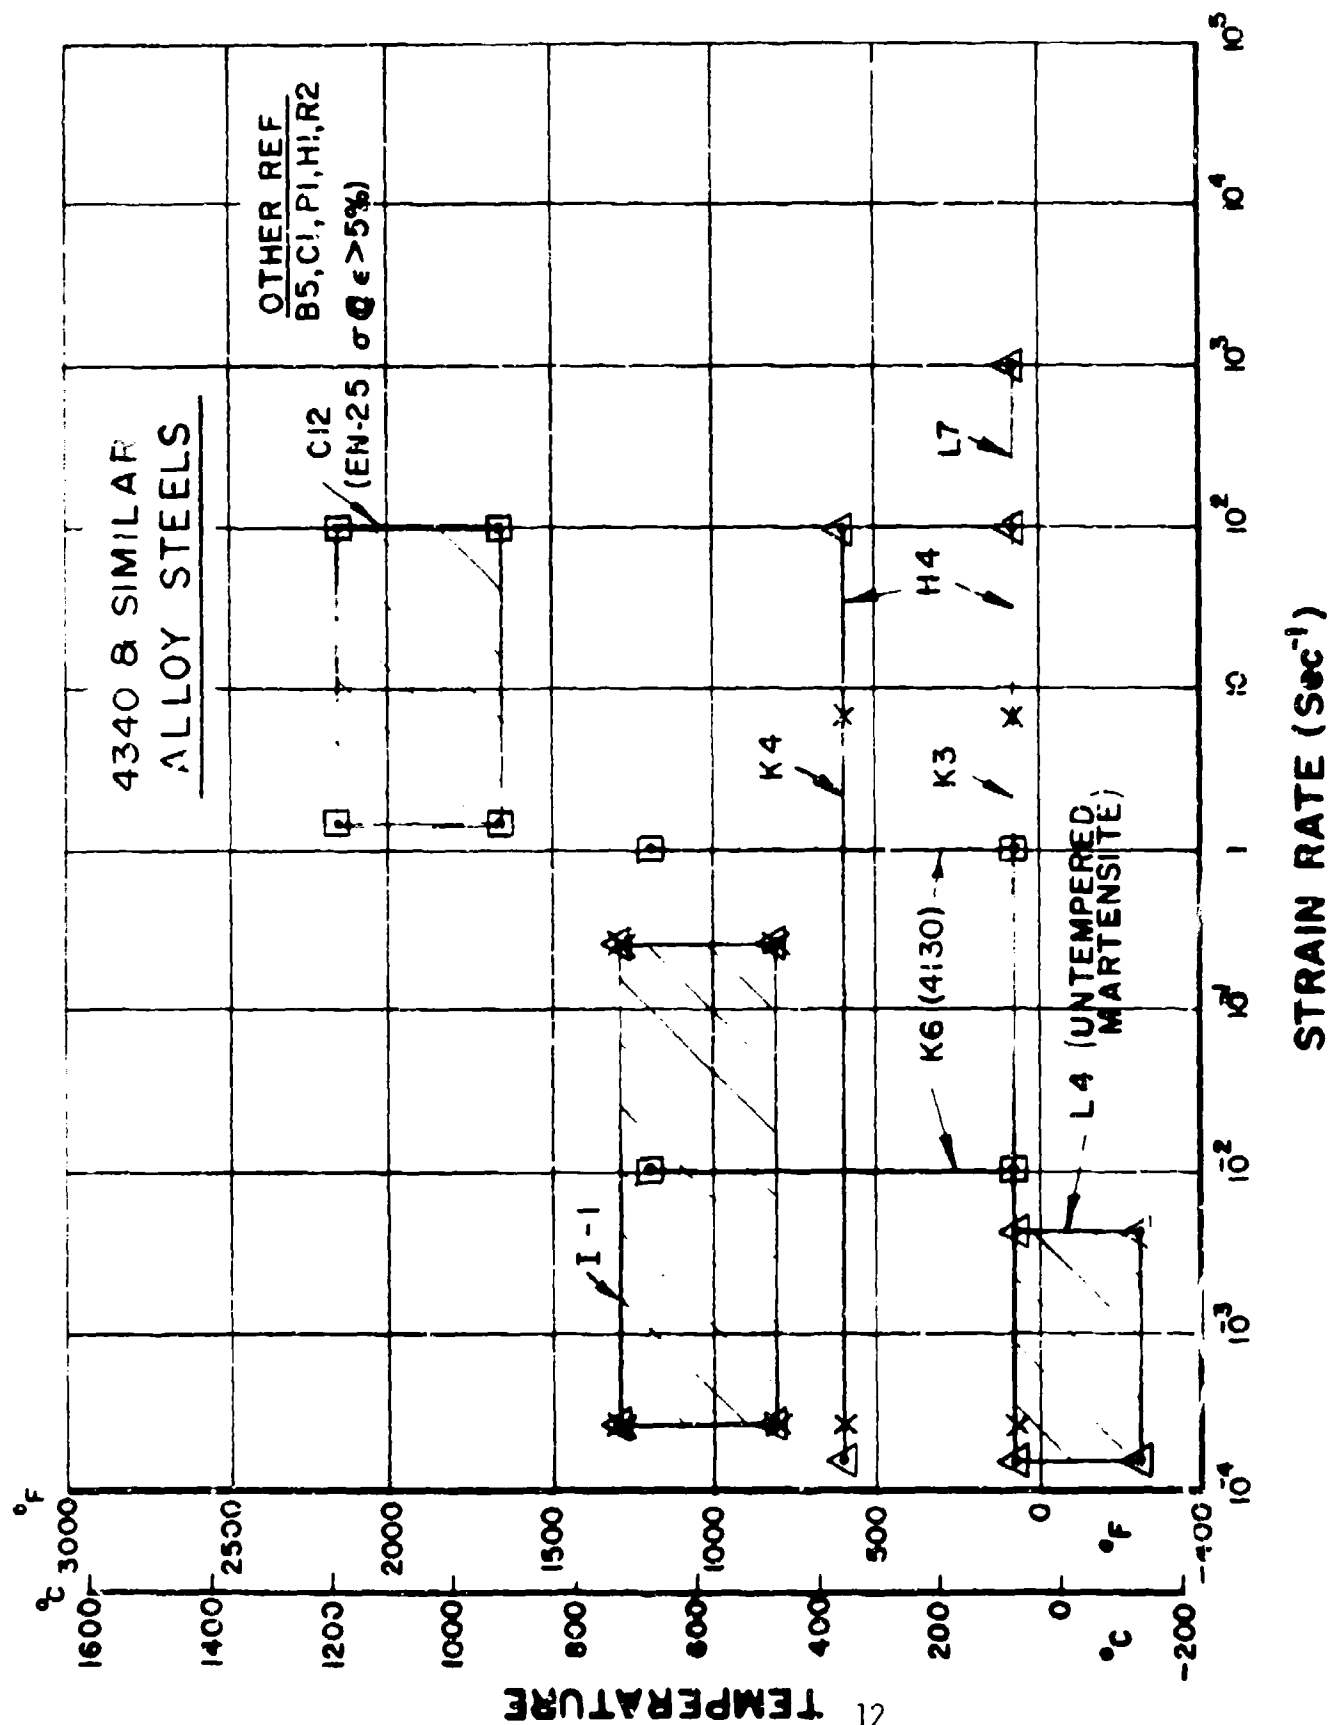


## Tool Steels

The strain rate sensitivity of the tool steels for which information is available is similar to that of the low alloy steels. At room temperature they are rate insensitive up to some transition strain rate above which they may show some rate sensitivity. Increasing temperature increases the transition rate for temperatures up to about 1000F. Above this an increasing rate sensitivity is found over the entire range of strain rates of interest. In the hot working temperature range the results are essentially the same as for alloy steels except that the stress levels are higher.

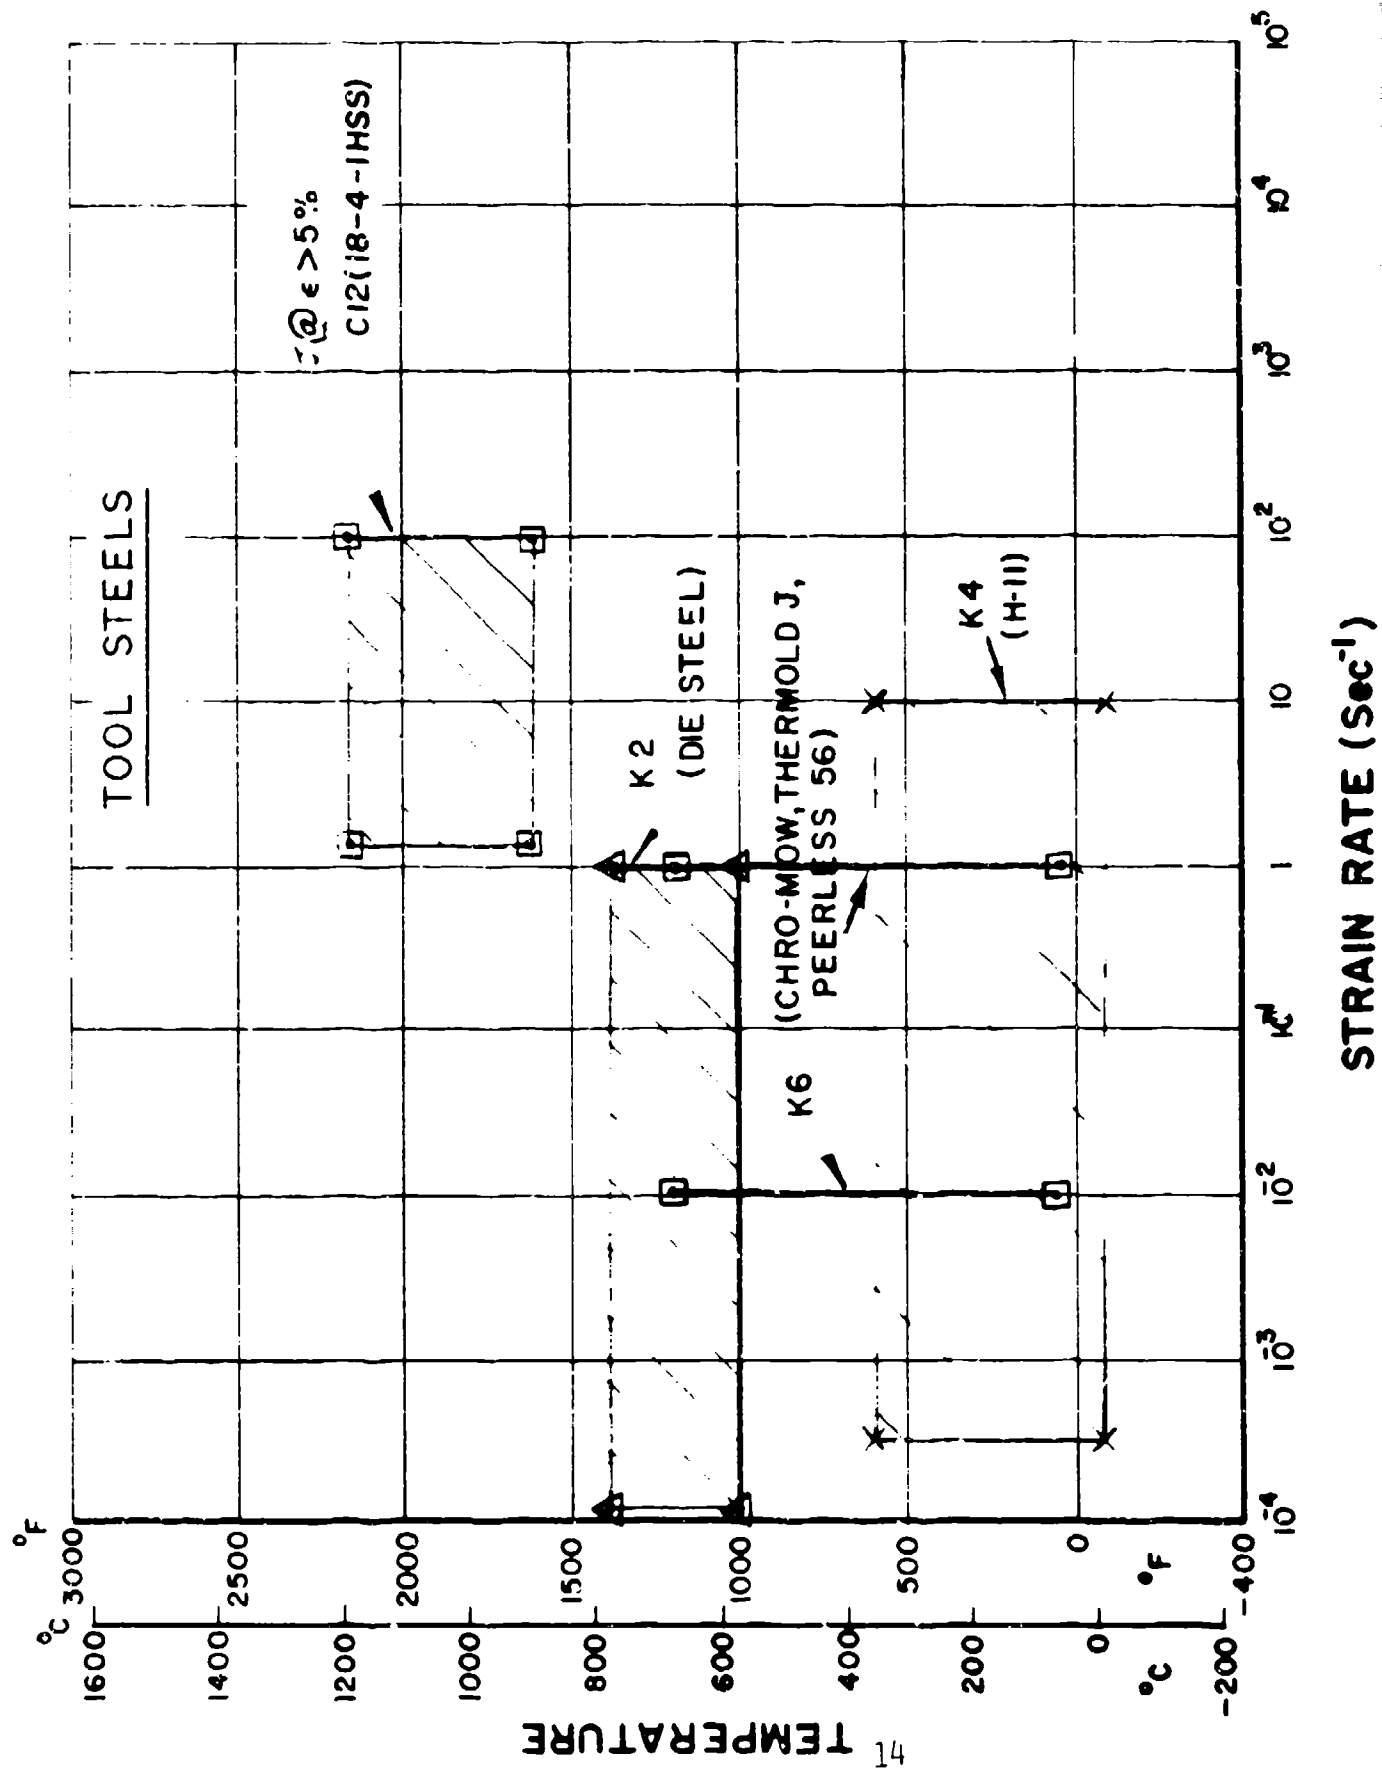

## Stainless Steels

The stainless steels that have been studied are generally rate insensitive at room temperature for all strain rates reported. At temperatures up to about 1000F they remain rate insensitive or possibly show a slight negative rate sensitivity in the 400 to 600 F range. At temperatures above 1000 F the static strength decreases rapidly and the material becomes increasingly rate sensitive.

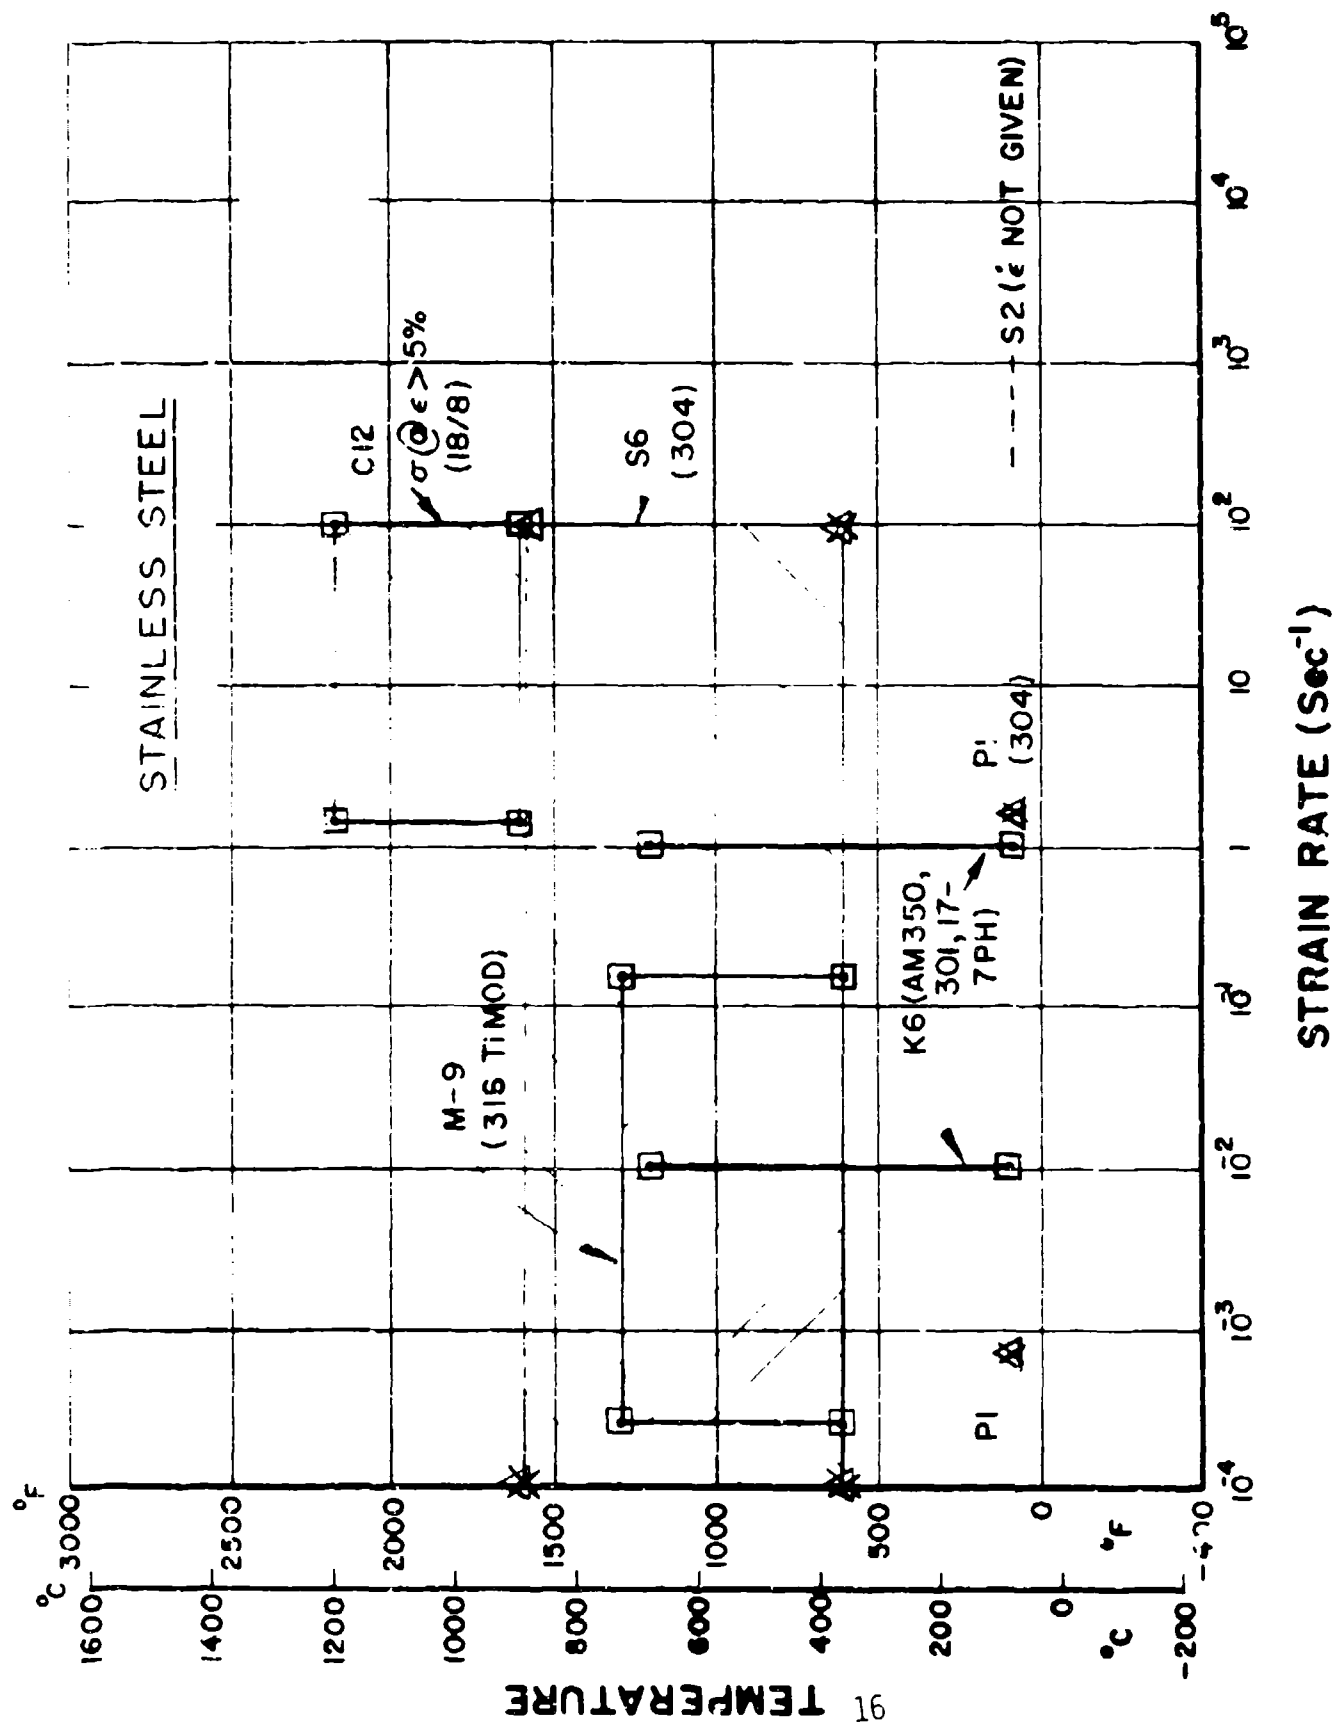




## Maraging Steels

There is a limited amount of data available on maraging steels. Room temperature results show a linear increase in yield strength with logarithmic strain rate in the range of strain rates from  $10^{-4}$  to  $10 \text{ sec}^{-1}$ . The 18% Ni-300 grade material shows a 10% increase in strength over this range and the 250 grade shows a 5% increase. The difference between yield and tensile strength is essentially constant or may decrease slightly at higher rates. At low temperatures the strain rate sensitivity is about the same as at room temperature.

At elevated temperatures there is a disagreement between the two available references. Ref. H4 shows the same rate sensitivity at temperatures up to 900 F as at room temperature. Ref. K4 shows a decreasing rate sensitivity with increasing temperature and an inverse sensitivity at 600 F. This results in a decrease in yield strength of about 5% for an increase in strain rate from  $10^{-4}$  to  $5.0 \text{ sec}^{-1}$ . This difference may be due to slight differences in the aging treatment or in heating rate and time at temperature.

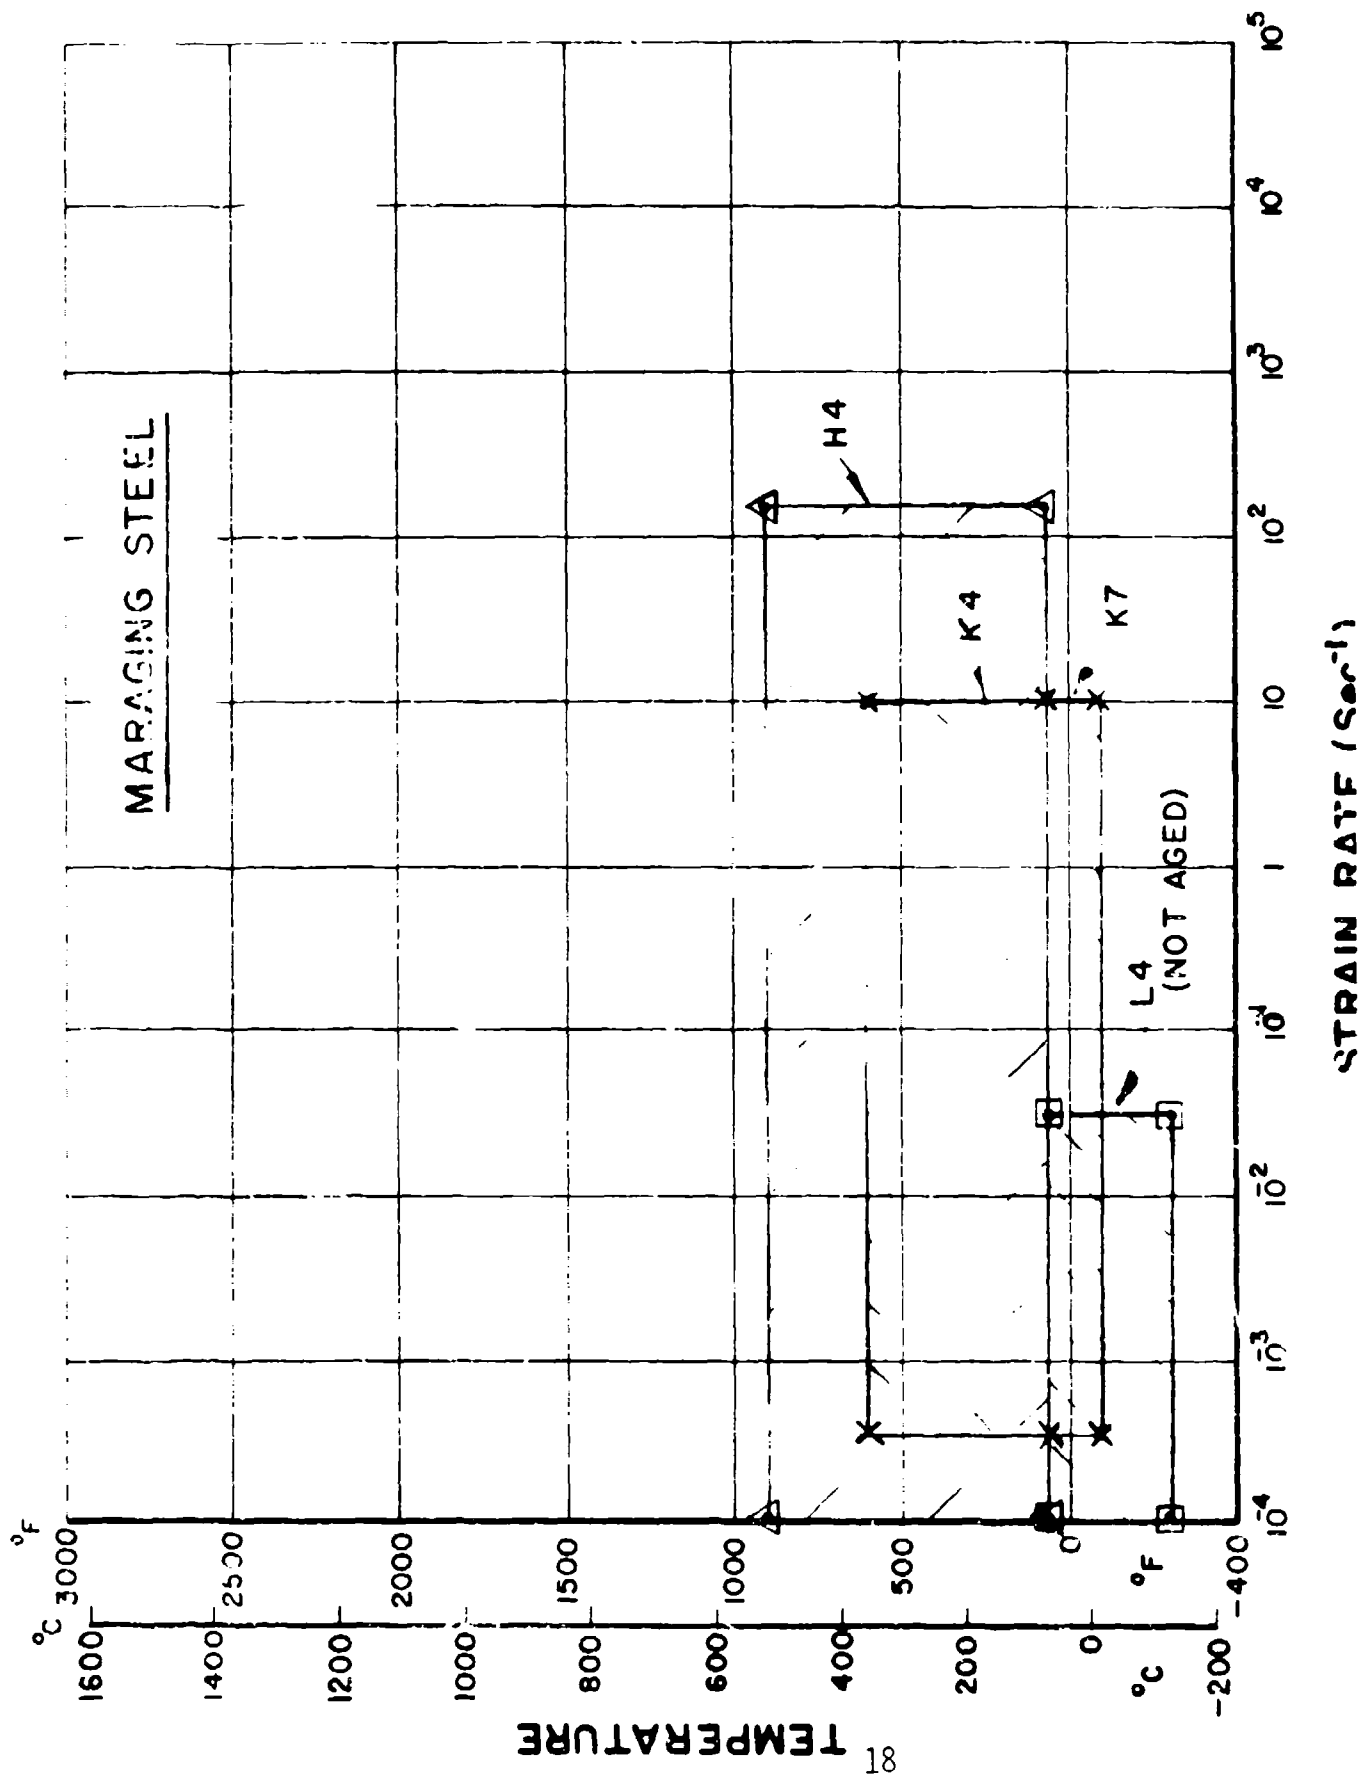


## ALUMINUM BASED MATERIALS

### Pure Aluminum Including 1100 Grade

Data on pure aluminum from 12 references were examined and general agreement of all of the references was found. At room temperature an approximately linear increase in flow stress with logarithmic strain rate was reported although some investigators reported an increase in the slope of the stress-strain rate curve at strain rates exceeding  $100 \text{ sec}^{-1}$ . The increase in flow stress with an increase in strain rate from  $10^{-3}$  to  $10^3 \text{ sec}^{-1}$  is generally about 15 to 20%. The strain rate sensitivity appears to be only slightly affected by plastic strain and by impurity content.

The effect of increasing temperature is a slight increase in the slope of the flow stress-log strain rate curve. Since the static strength decreases rapidly with temperature this results in a significant increase in relative rate sensitivity. At 750 F the flow stress increases by a factor of 3 with a strain rate increase from  $10^{-3}$  to  $10^3 \text{ sec}^{-1}$ .


The effect of strain rate changes are considered in references F2 and N2.

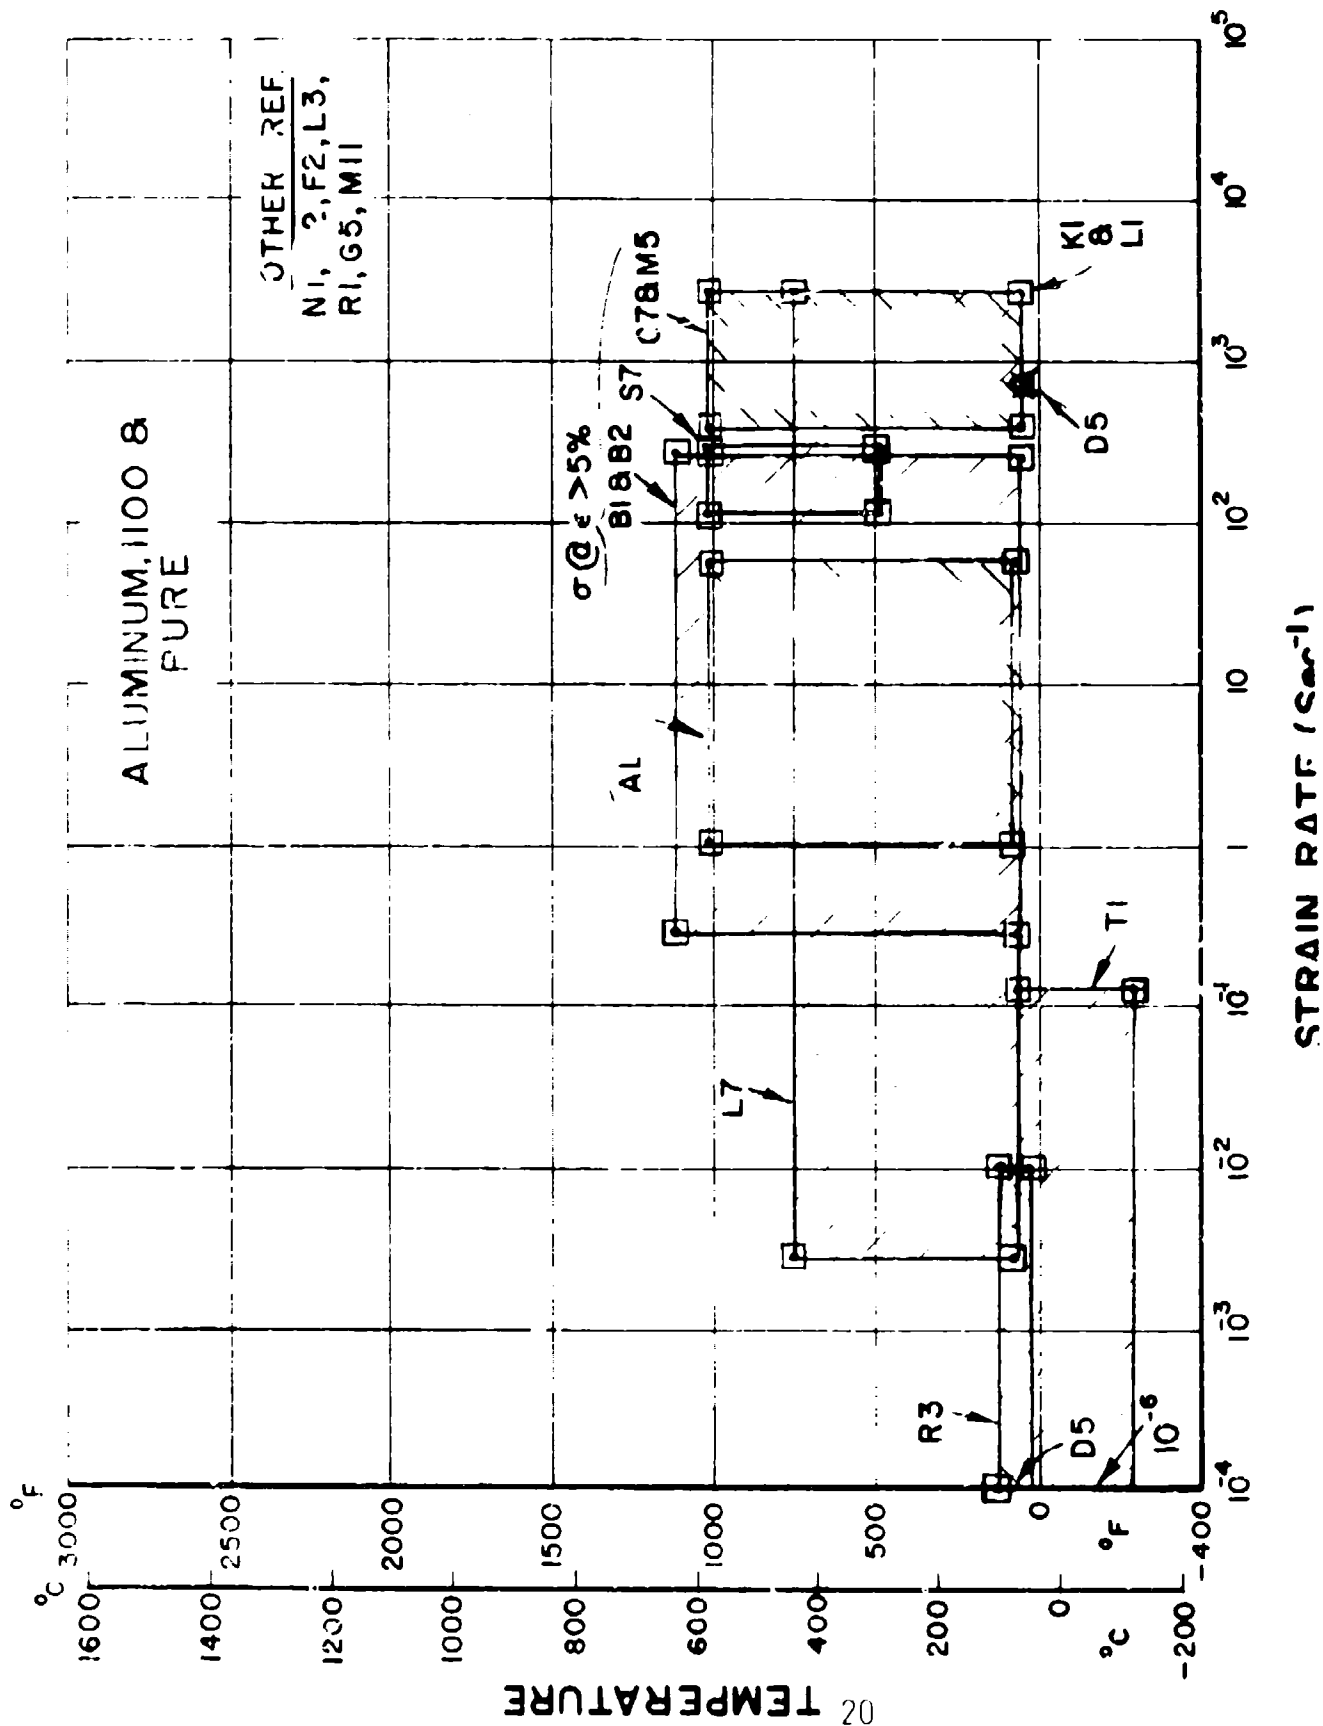

## 6061 Aluminum Alloy

All available data on this material is for the T6 or fully aged condition. For strain rates less than  $10 \text{ sec}^{-1}$  at room temperature this material is almost completely rate insensitive. At higher strain rates some investigators (A3 and H4) have reported a rate sensitive region with a 20% increase in strength between 10 and  $10^3 \text{ sec}^{-1}$ . Other investigators (M4 and G5) have found no rate sensitivity up to a strain rate of  $10^3 \text{ sec}^{-1}$ .


The only data on this material at elevated temperatures is in reference H3 (same data as H4). This gives a significant positive rate sensitivity at 500 and 700 F and at strain rates from 1 to  $10^2 \text{ sec}^{-1}$ . At 700 F the tensile strength increases from 10 to 35 ksi over this strain rate range.

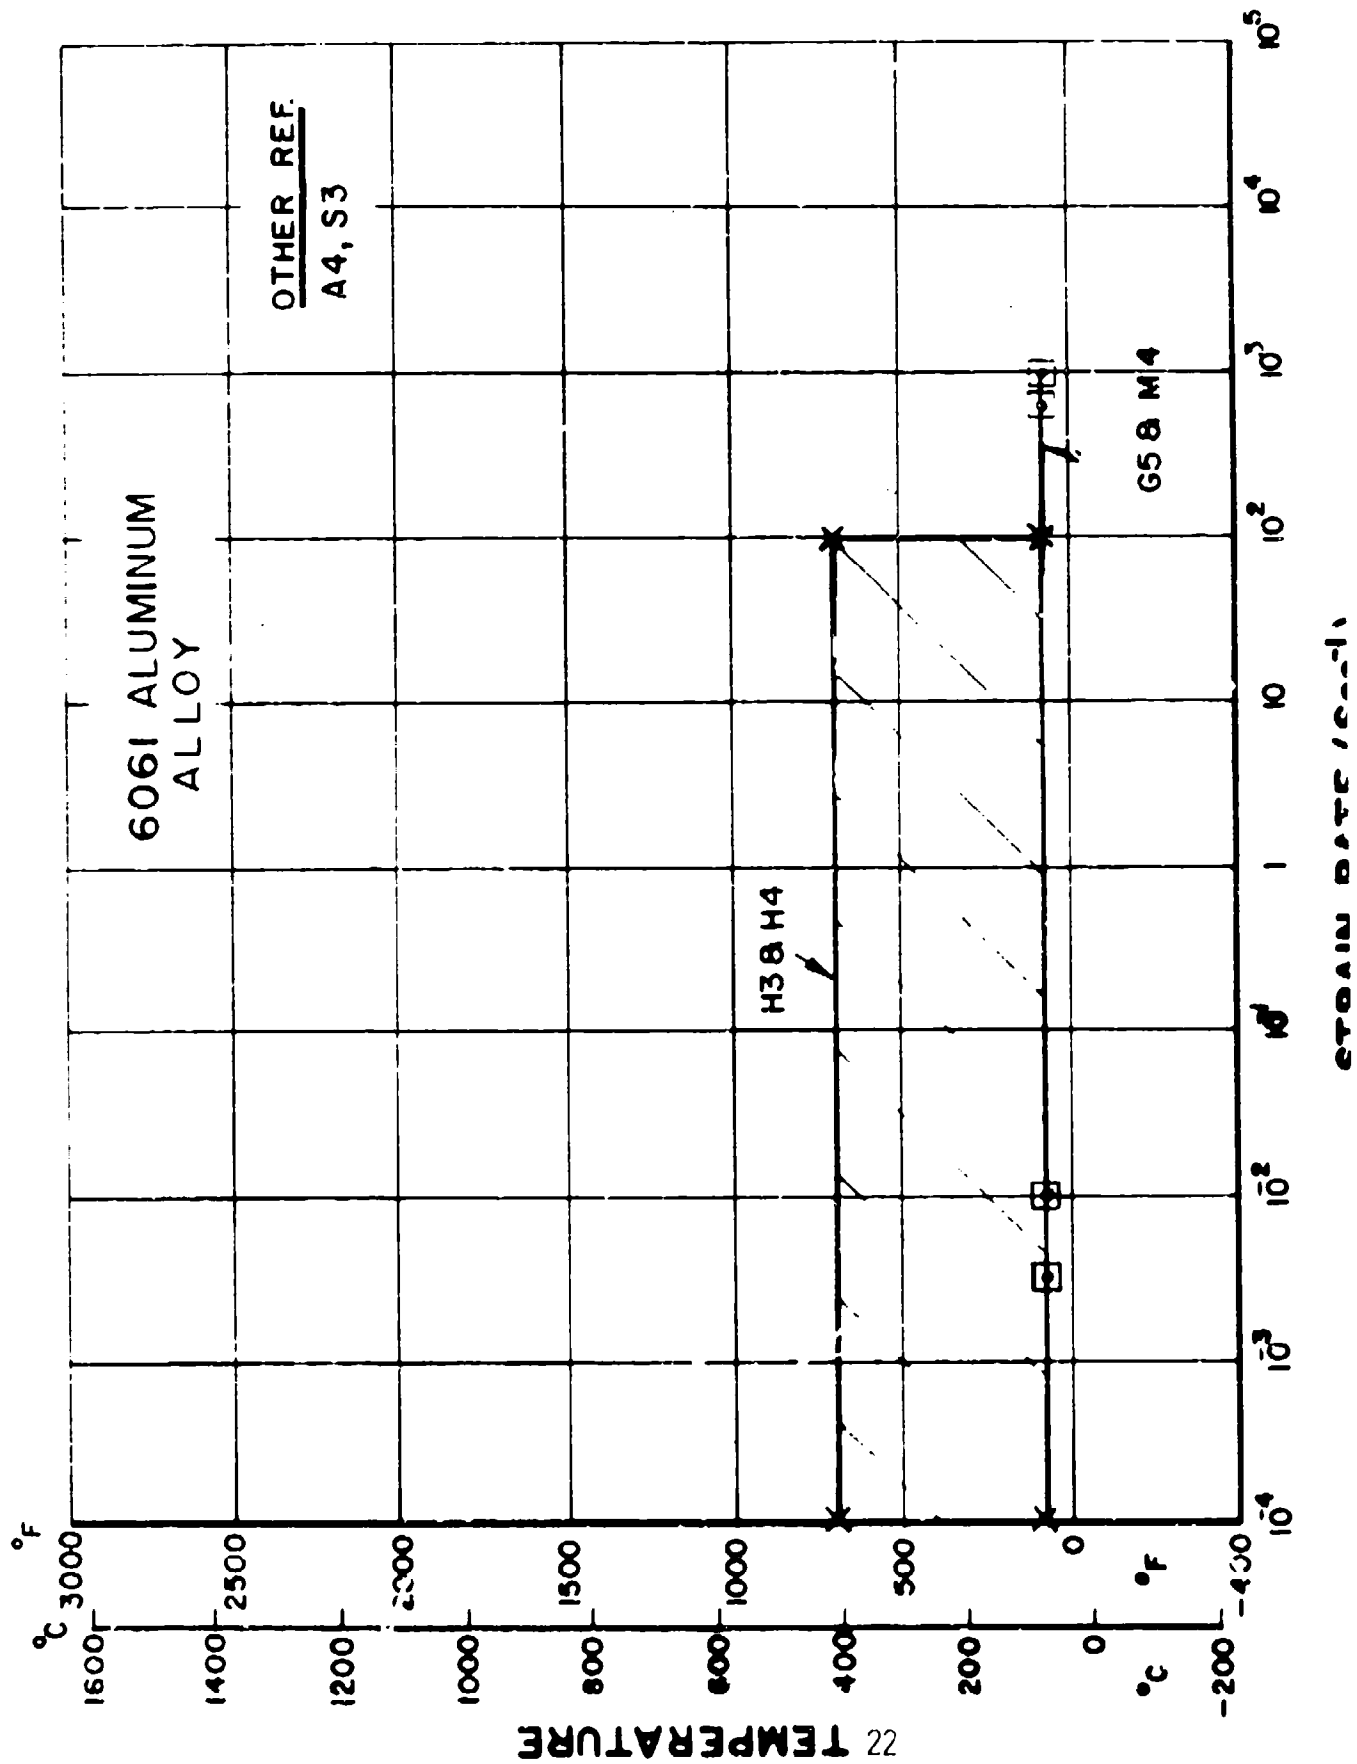

### 7075 Aluminum Alloy

The results available for the T6 condition are essentially the same as for 6061-T6 as discussed above, except that the stress values are somewhat higher.

In the annealed or "O" condition (not solution annealed) this alloy shows rate insensitive behavior below  $10^{-2}$  sec $^{-1}$  at room temperature and increasing positive sensitivity at higher temperatures. At all temperatures an increase in rate sensitivity is found at strain rates above  $10^{-2}$  sec $^{-1}$ .

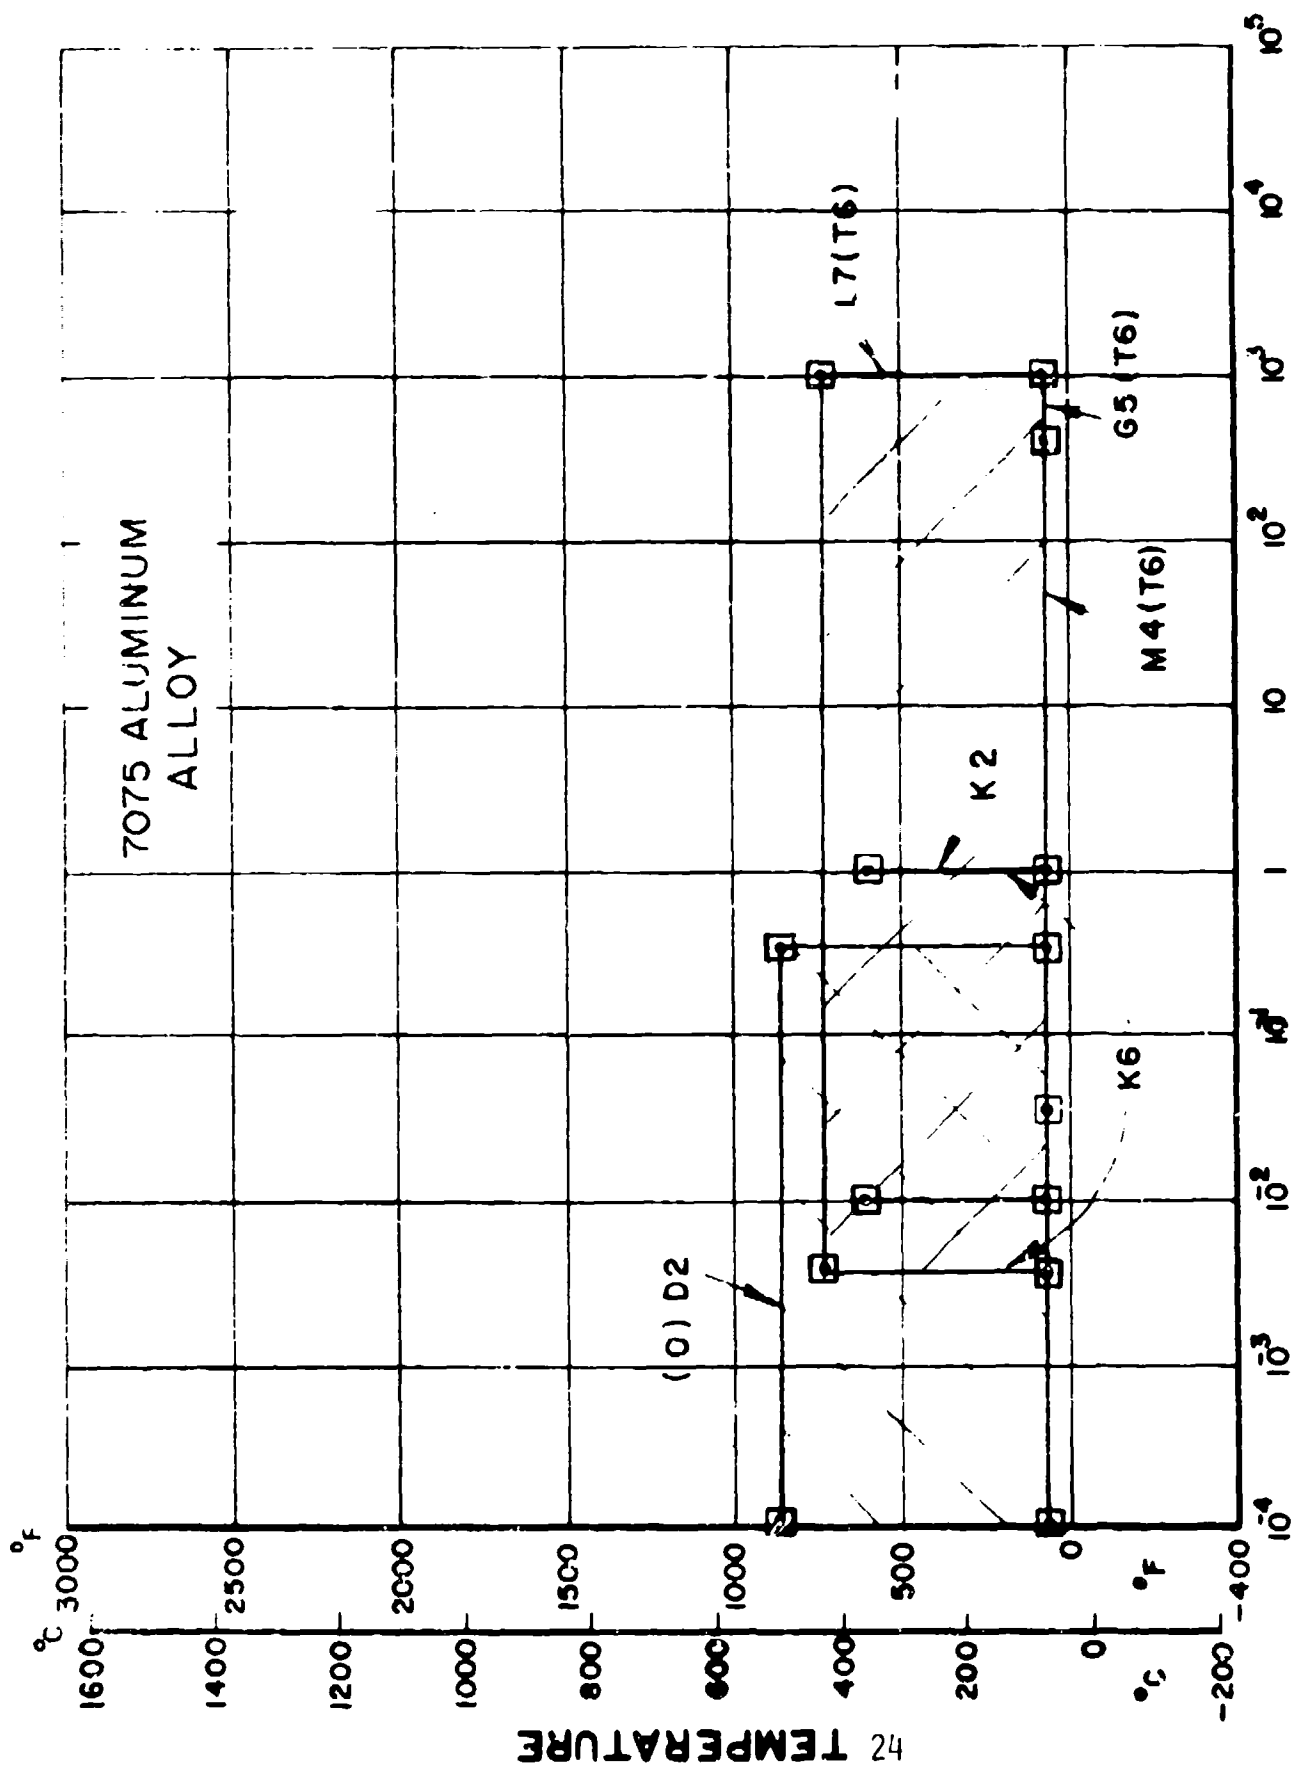


STANDARD DATA 10-11



### Other Aluminum Alloys


Available data on 2024-T4, 2024-T3, 2014-T6 and 5024-H34 all show similar results to those for 6061-T6. These alloys are all essentially rate insensitive at temperatures below 300 F and strain rates below  $10^2 \text{ sec}^{-1}$ . At higher temperatures some positive rate sensitivity is found. Since these temperatures are generally above the aging temperatures for these alloys, overaging reactions are taking place at these test temperatures. Therefore, the properties will depend on time at temperature as well as strain rate and temperature.

A 3003 alloy in the solution annealed condition has been shown to exhibit three regions of rate sensitivity at room temperature (H-7). It is rate insensitive up to a strain rate of  $2 \times 10^{-2} \text{ sec}^{-1}$  and then has a positive rate sensitivity up to about  $10^{-1} \text{ sec}^{-1}$ . Above this rate a negative rate sensitivity was found. A negative rate sensitivity was also found in a 2024 alloy in the solution annealed condition at room temperature and strain rates ranging from  $10^{-2}$  to  $0.3 \text{ sec}^{-1}$ . This is attributed to a type of dynamic strain aging or structural deformational instability. During low strain rate deformation, the strain in the material triggers changes in the solute configurations which result in increased resistance to dislocation motion. At high strain rates there is not sufficient time for these solute configurational changes to occur resulting in less resistance to dislocation motion and thus lower strength.

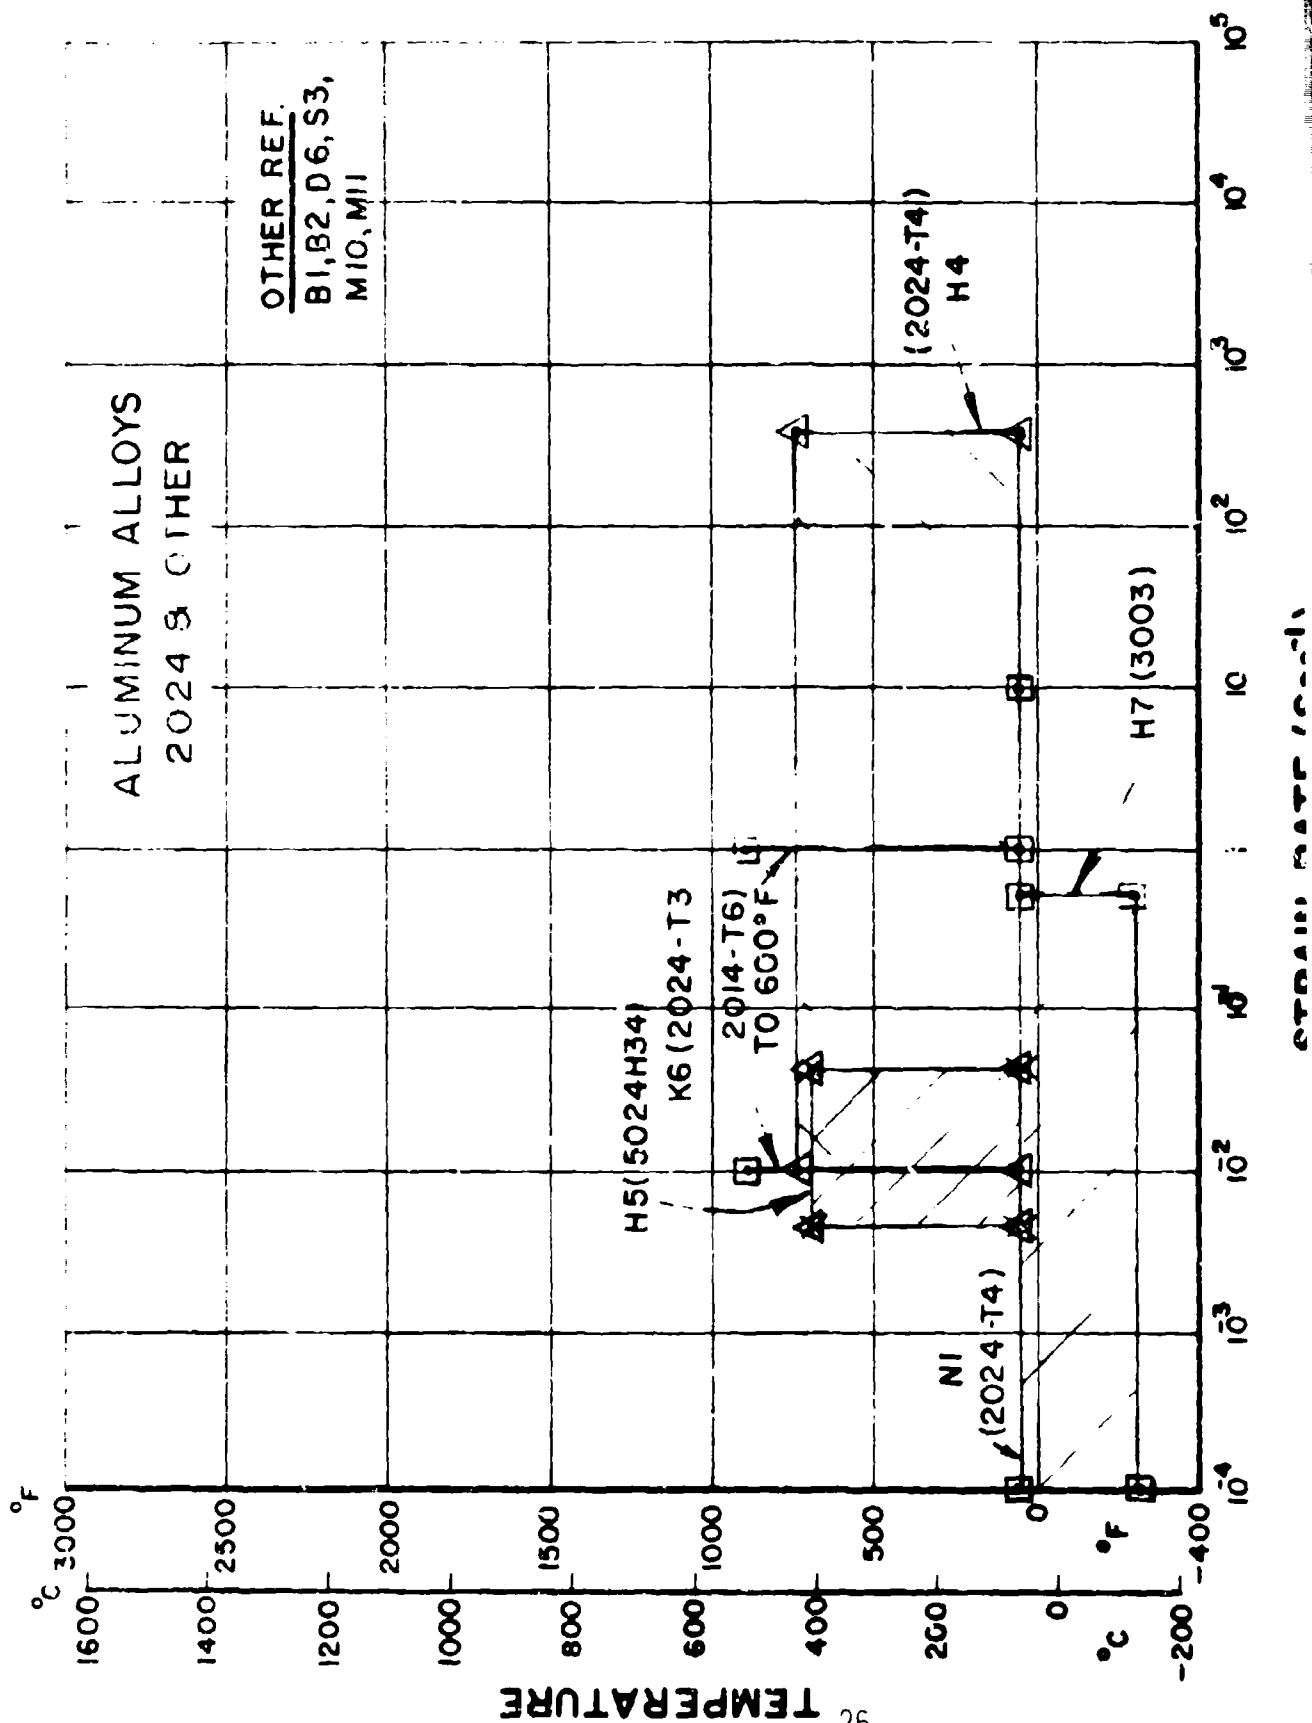

## MAGNESIUM ALLOYS

Reference F1 gives results for 18 different magnesium base alloys at strain rates up to  $0.08 \text{ sec}^{-1}$  and temperatures to 900 F. Most of the alloys showed very little rate sensitivity at room temperature except for AZ80Z-T5, ZK60A-T5 and M1AF which showed a 20 percent increase in strength over the range of strain rates used. At elevated temperatures a general increase in rate sensitivity was reported for all alloys with generally linear increases in strength with logarithmic strain rate. The other available references on magnesium alloys give similar results with only a slight increase, if any, in the rate sensitivity at higher strain rates up to  $10^3 \text{ sec}^{-1}$ . Reference L7 reports an interesting difference between the results for tension and compression loading.

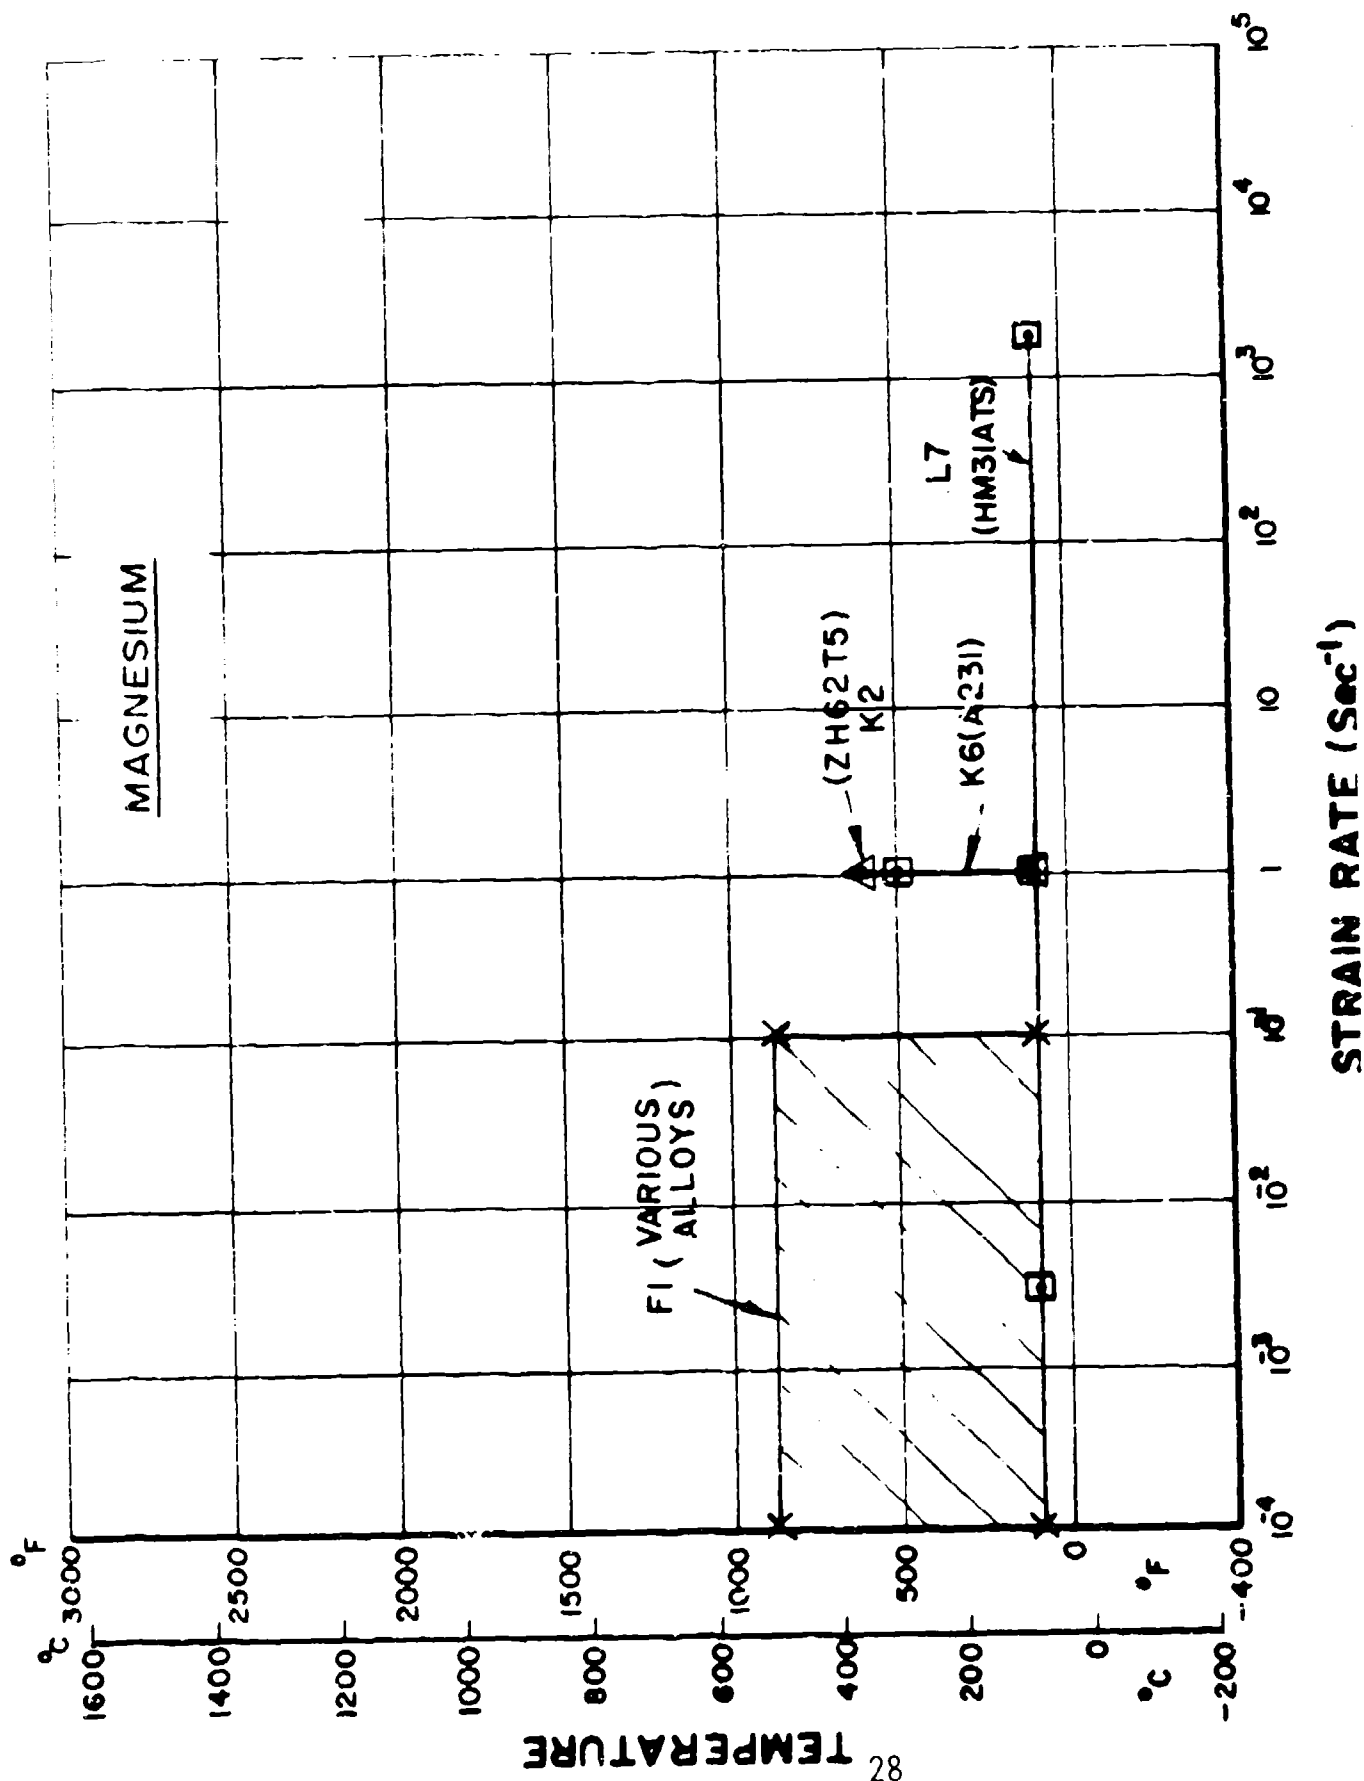

## TITANIUM ALLOYS


### Titanium-6Al, 4V Alloy

There are four major references for this material. They all show this material to be moderately rate sensitive but there is some disagreement as to the shape of the flow stress-strain rate curve. Two references show almost no rate sensitivity at strain rates below  $10 \text{ sec}^{-1}$  while the other two show about a 10 percent increase between  $10^{-3}$  and  $10 \text{ sec}^{-1}$ . All references show an increase in rate sensitivity above  $10 \text{ sec}^{-1}$  with a 10 percent increase in strength between  $10$  and  $10^3 \text{ sec}^{-1}$ .

The results at elevated temperatures up to 1000 F are approximately parallel to those at room temperature.

This material is usable in either the solution annealed condition or in an artificially aged condition. The strain rate sensitivity is essentially the same in both conditions.

Other factors considered are notched strength (B4) and biaxial stress (L8).

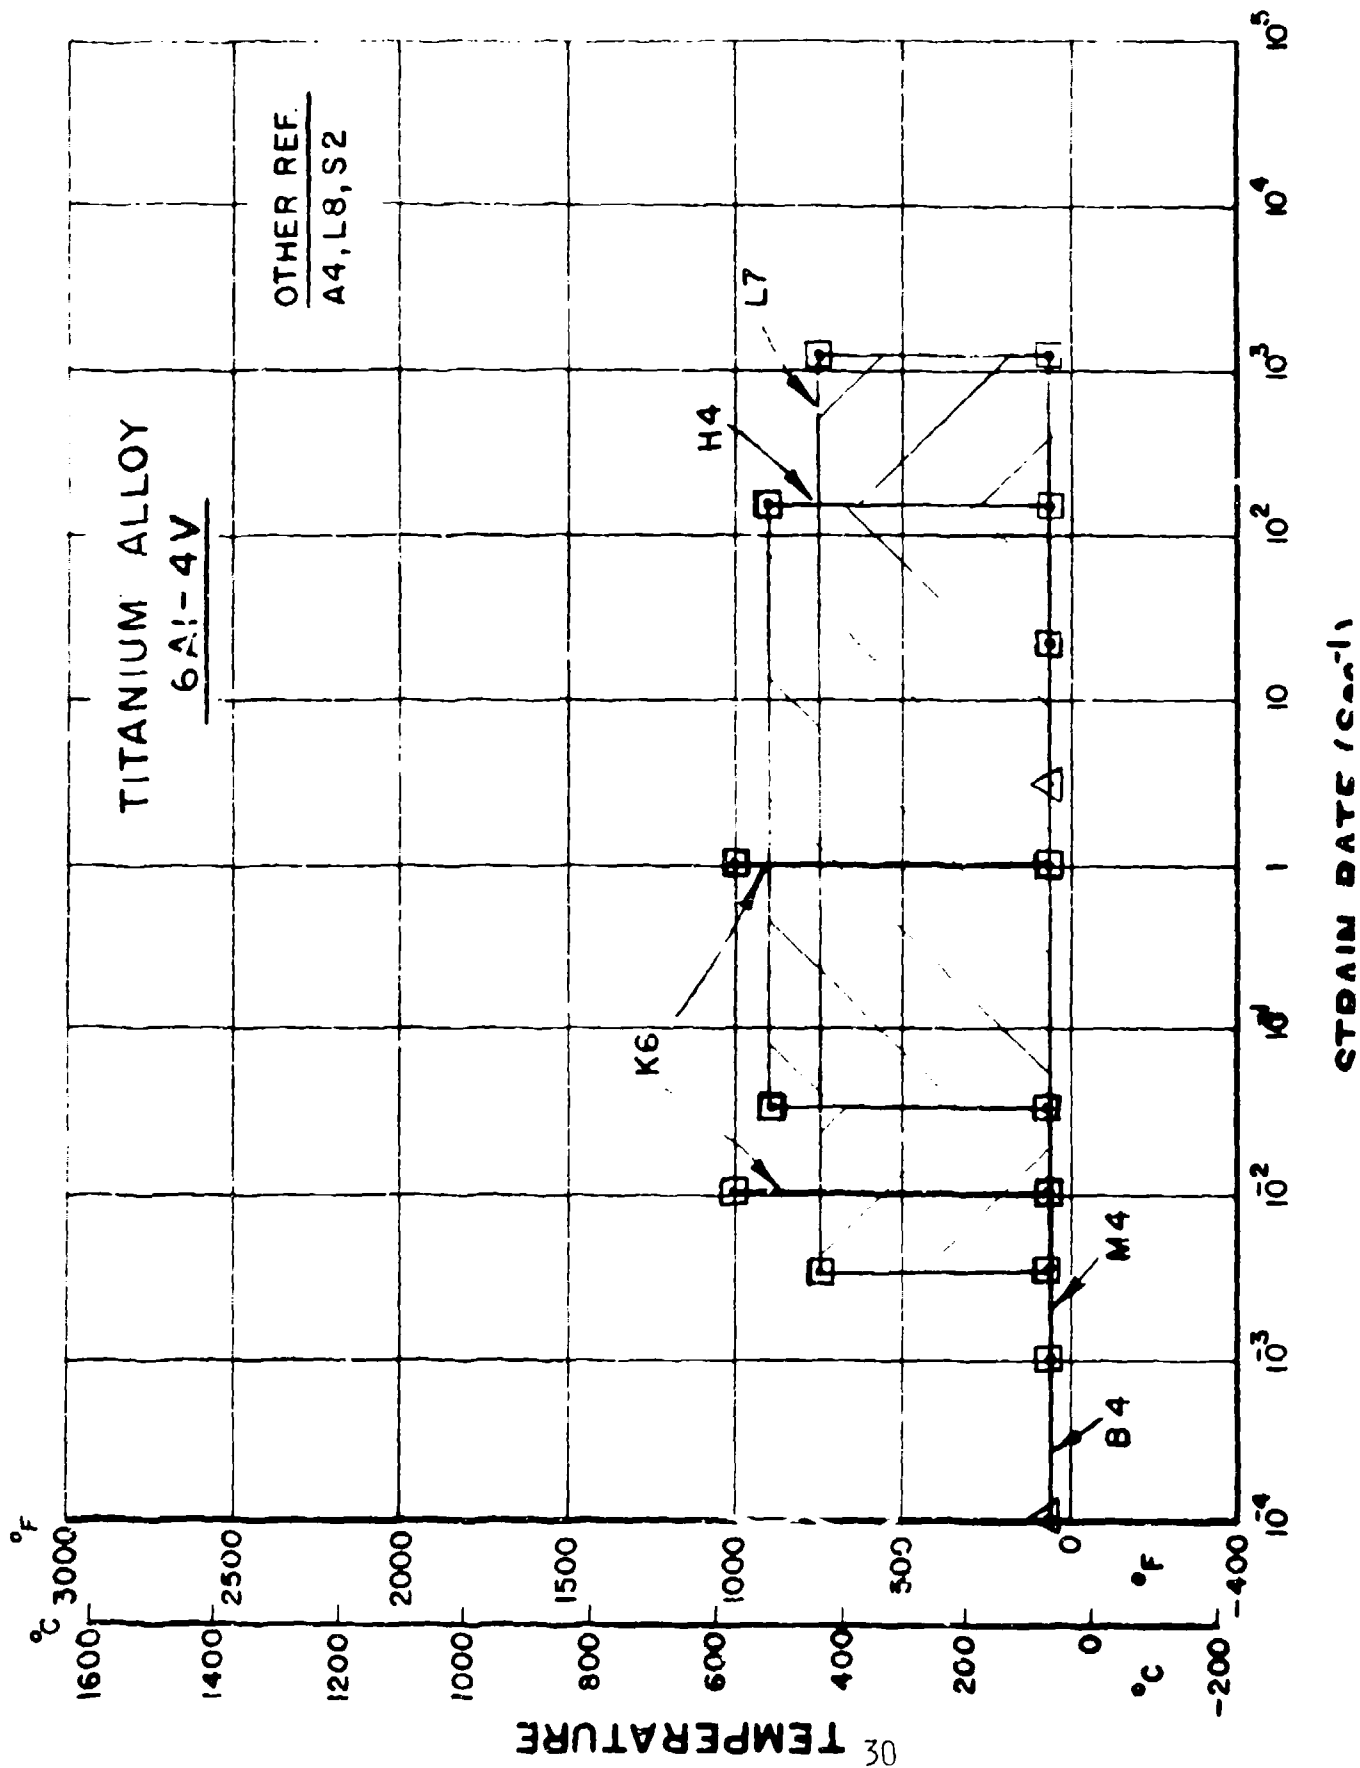


### Other Titanium Alloys

Results for several commercially pure titanium alloys such as 50 A, 55A and 70A are available and all show about the same or slightly higher rate sensitivity than that for the 6Al-4V alloy. At elevated temperatures the rate sensitivity is somewhat greater than at room temperature particularly in the 400 to 600 F range.

Other high strength alloys studied are 5 Al-2.5 Sn, 8Al-1Mo-1V, 4Al-3Mo-1V, 5.7Al-2.7Sn(A-110-AT), 1.8Fe-1.8Cr-1.5Mo(140A), 13V-11Cr-3Al, and 8Al,2Cb,Ta. All of these show rate sensitivities very similar to the 6Al-4V alloy.

It appears that titanium alloys are unique in that the strain rate sensitivity does not decrease significantly as the strength is increased by either alloying or heat treatment. This is contrary to the behavior of virtually all other common structural metals.

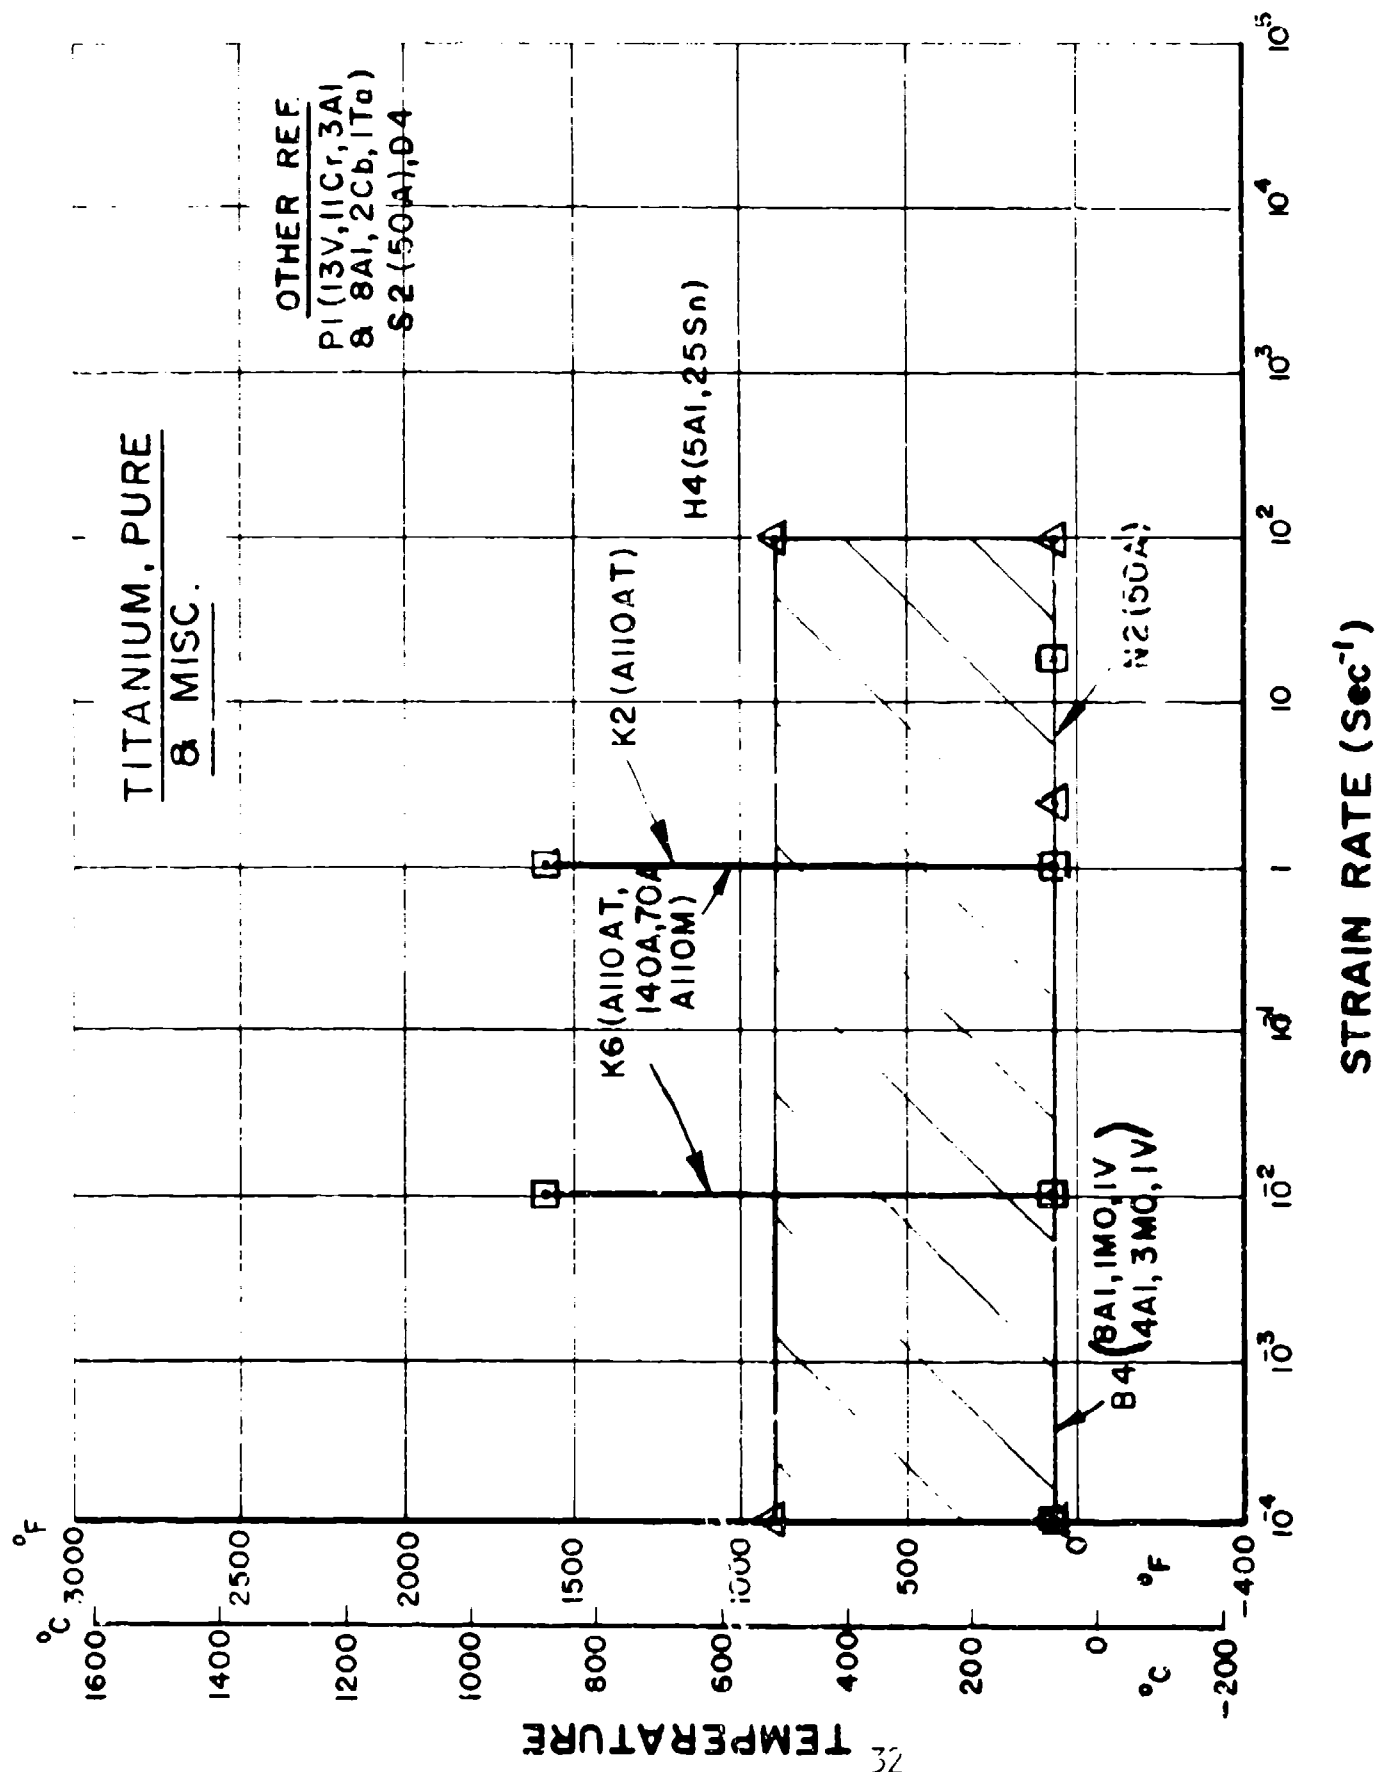




## Copper

With the exception of one data point, all of the available data on copper alloys is for high purity or commercially pure copper. No data on brasses or bronzes have been located.

In the fully annealed condition, the yield stress and flow stress of copper at low strain values are only slightly rate sensitive. The strength increases 10 to 20 percent over the range of strain rates from  $10^{-3}$  to  $10^3 \text{ sec}^{-1}$ . The rate sensitivity increases with increasing strain values. The rate sensitivity also increases with prior cold working. For copper that has been cold worked to a yield strength of about 40,000 psi, strength increases ranging from 30 to 60 percent have been reported over the range of strain rates from  $10^{-3}$  to  $10^3 \text{ sec}^{-1}$ . The flow stress is generally a linear function of logarithmic strain rate over this range.

At elevated temperatures the flow stress-strain rate curves are parallel to the room temperature curves but at lower stress levels.


The only other copper alloy studied is beryllium copper (S3) which showed no significant rate sensitivity at  $10^2 \text{ sec}^{-1}$  and at room temperatures.

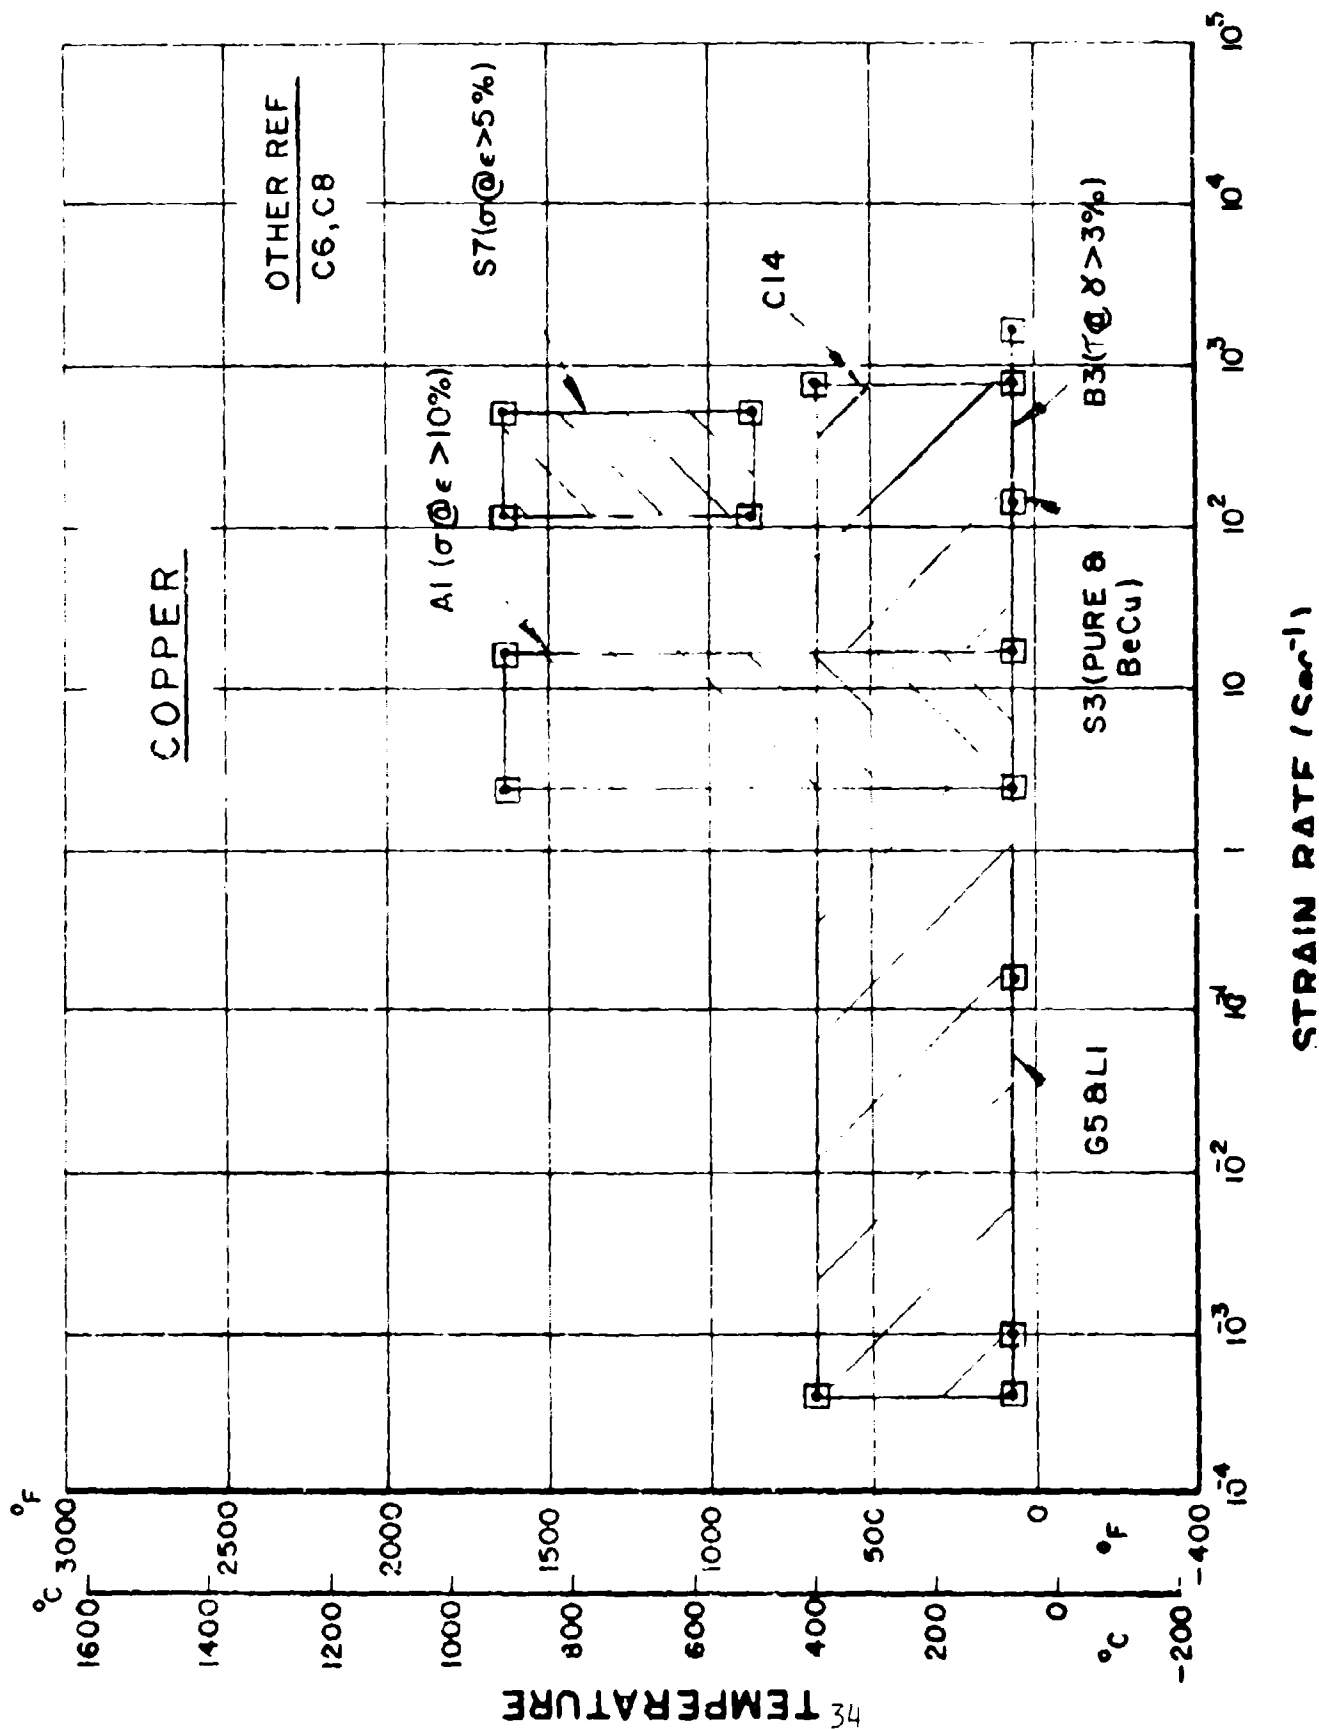

## Lead

The flow stress of lead is fairly rate sensitive at room temperature. At small strain values (2 to 3 percent) the flow stress increases by 40 to 60 percent over the range of strain rates from  $10^{-3}$  to  $10^3 \text{ sec}^{-1}$ . At higher strain values the rate sensitivity increases with an increase in flow stress of up to 75 percent reported for the same strain rate range, at 30 percent strain. The flow stress is a linear function of logarithmic strain rate over this range.

No results for temperatures other than room temperature were found.

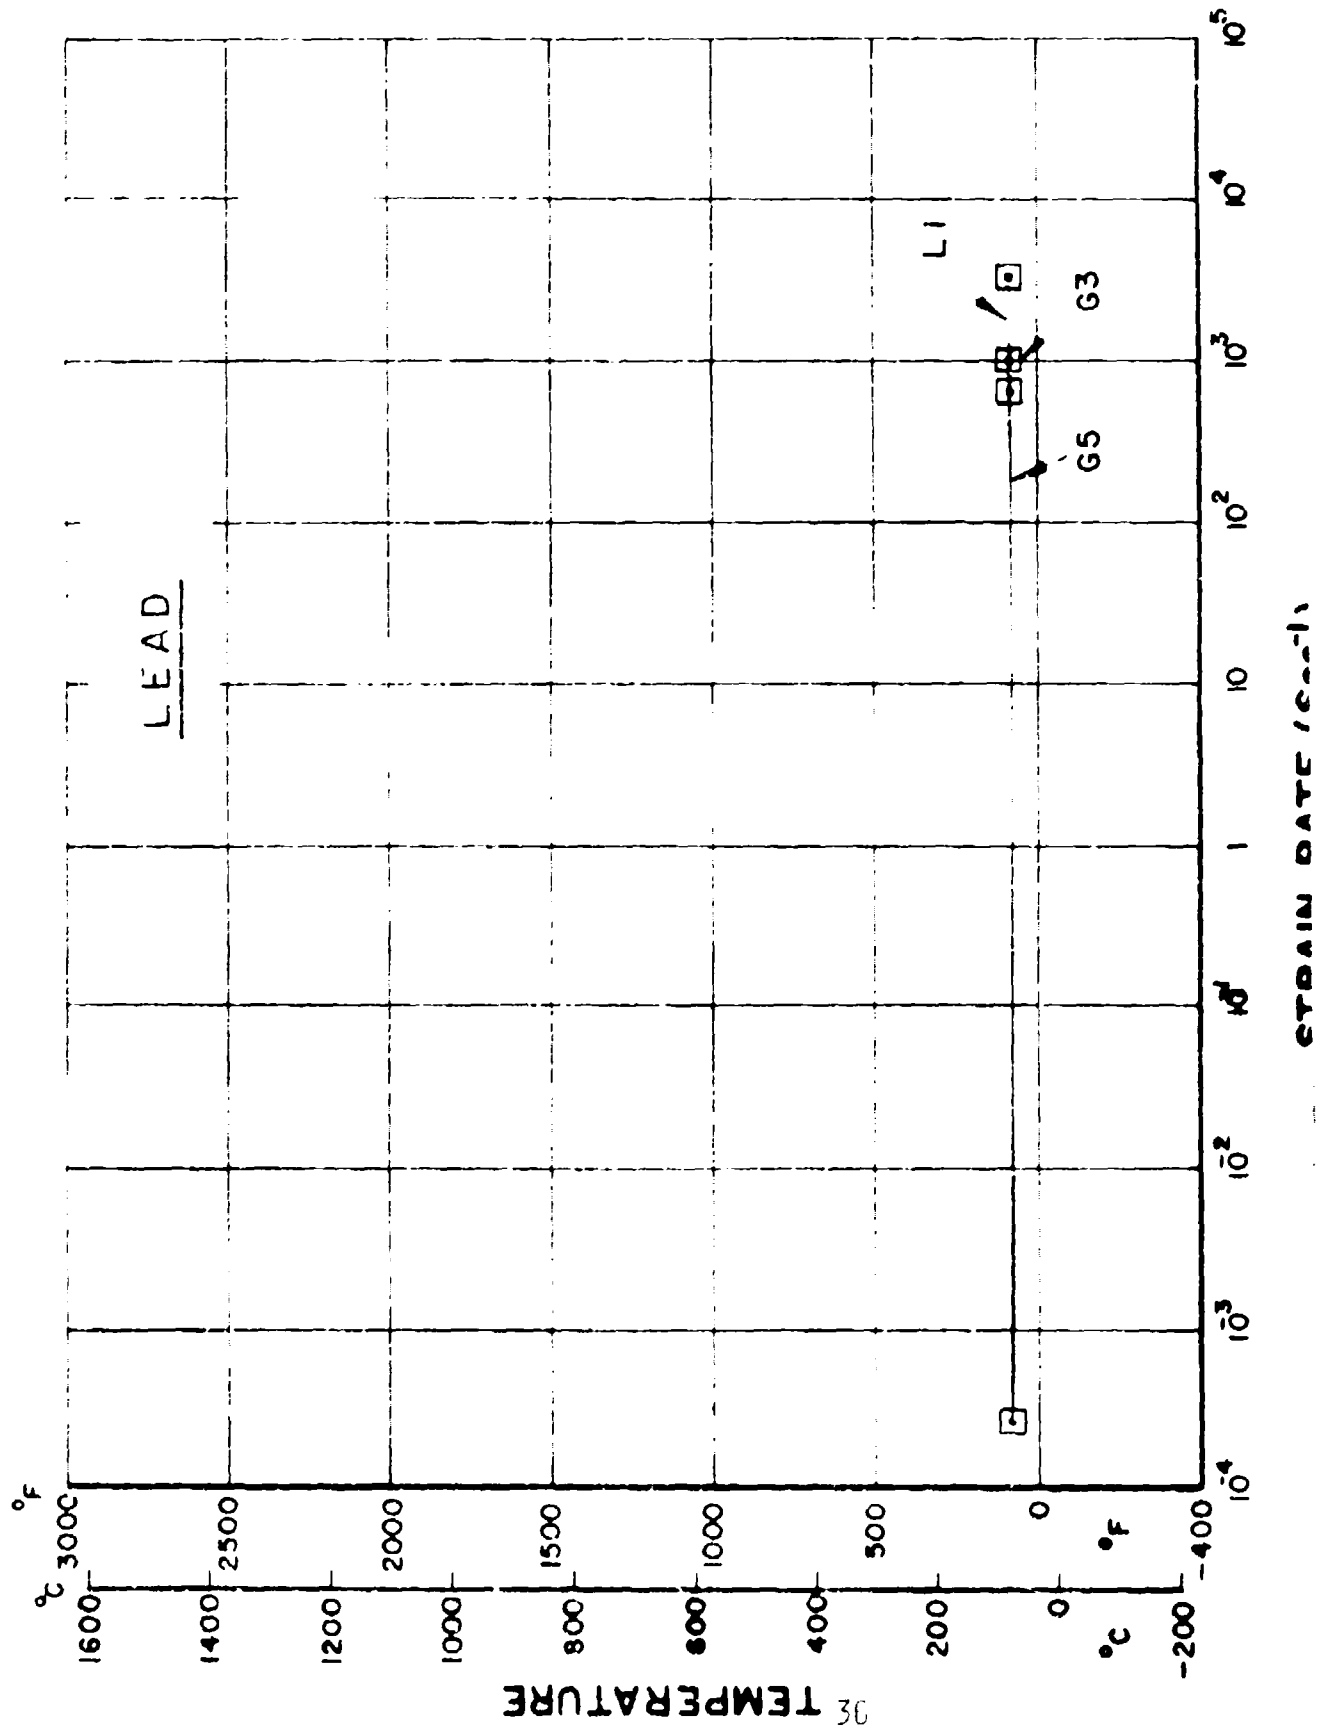


TEMPERATURE 30

## NICKEL AND NICKEL BASE ALLOYS

Only two references report results for pure nickel. In the annealed condition it is moderately rate sensitive with about a 20 percent increase in strength over the strain rate range from  $10^{-3}$  to  $10^3 \text{ sec}^{-1}$  for all strain values. In the cold worked condition it is slightly more rate sensitive. At temperatures up to 500 C the flow stress-strain rate curves are essentially parallel to the room temperature.

Results are available for four nickel base "superalloys". These are Udimet 700, Unitemp 1753, Mar-M200 (single crystals) and Inconel -X. The curve of strength versus temperature at strain rates in the order of  $10^{-3} \text{ sec}^{-1}$  for all of these materials has a characteristic shape. The strength is essentially constant from room temperature to some temperature in the range of 1200 to 1400F. In this region they are essentially rate insensitive or have a slight negative rate sensitivity near the upper end of this range. Above this temperature the strength drops rapidly until it reaches about 10 ksi at a temperature of about 2000 to 2200 F. In the middle of this decreasing strength range the strength is highly rate sensitive with increases of 30 to 40 ksi reported over the range of strain rates from  $10^{-3}$  to  $1.0 \text{ sec}^{-1}$ . At the higher temperatures, the absolute rate sensitivity decreases but due to the very low static strength the relative rate sensitivity is about the same.

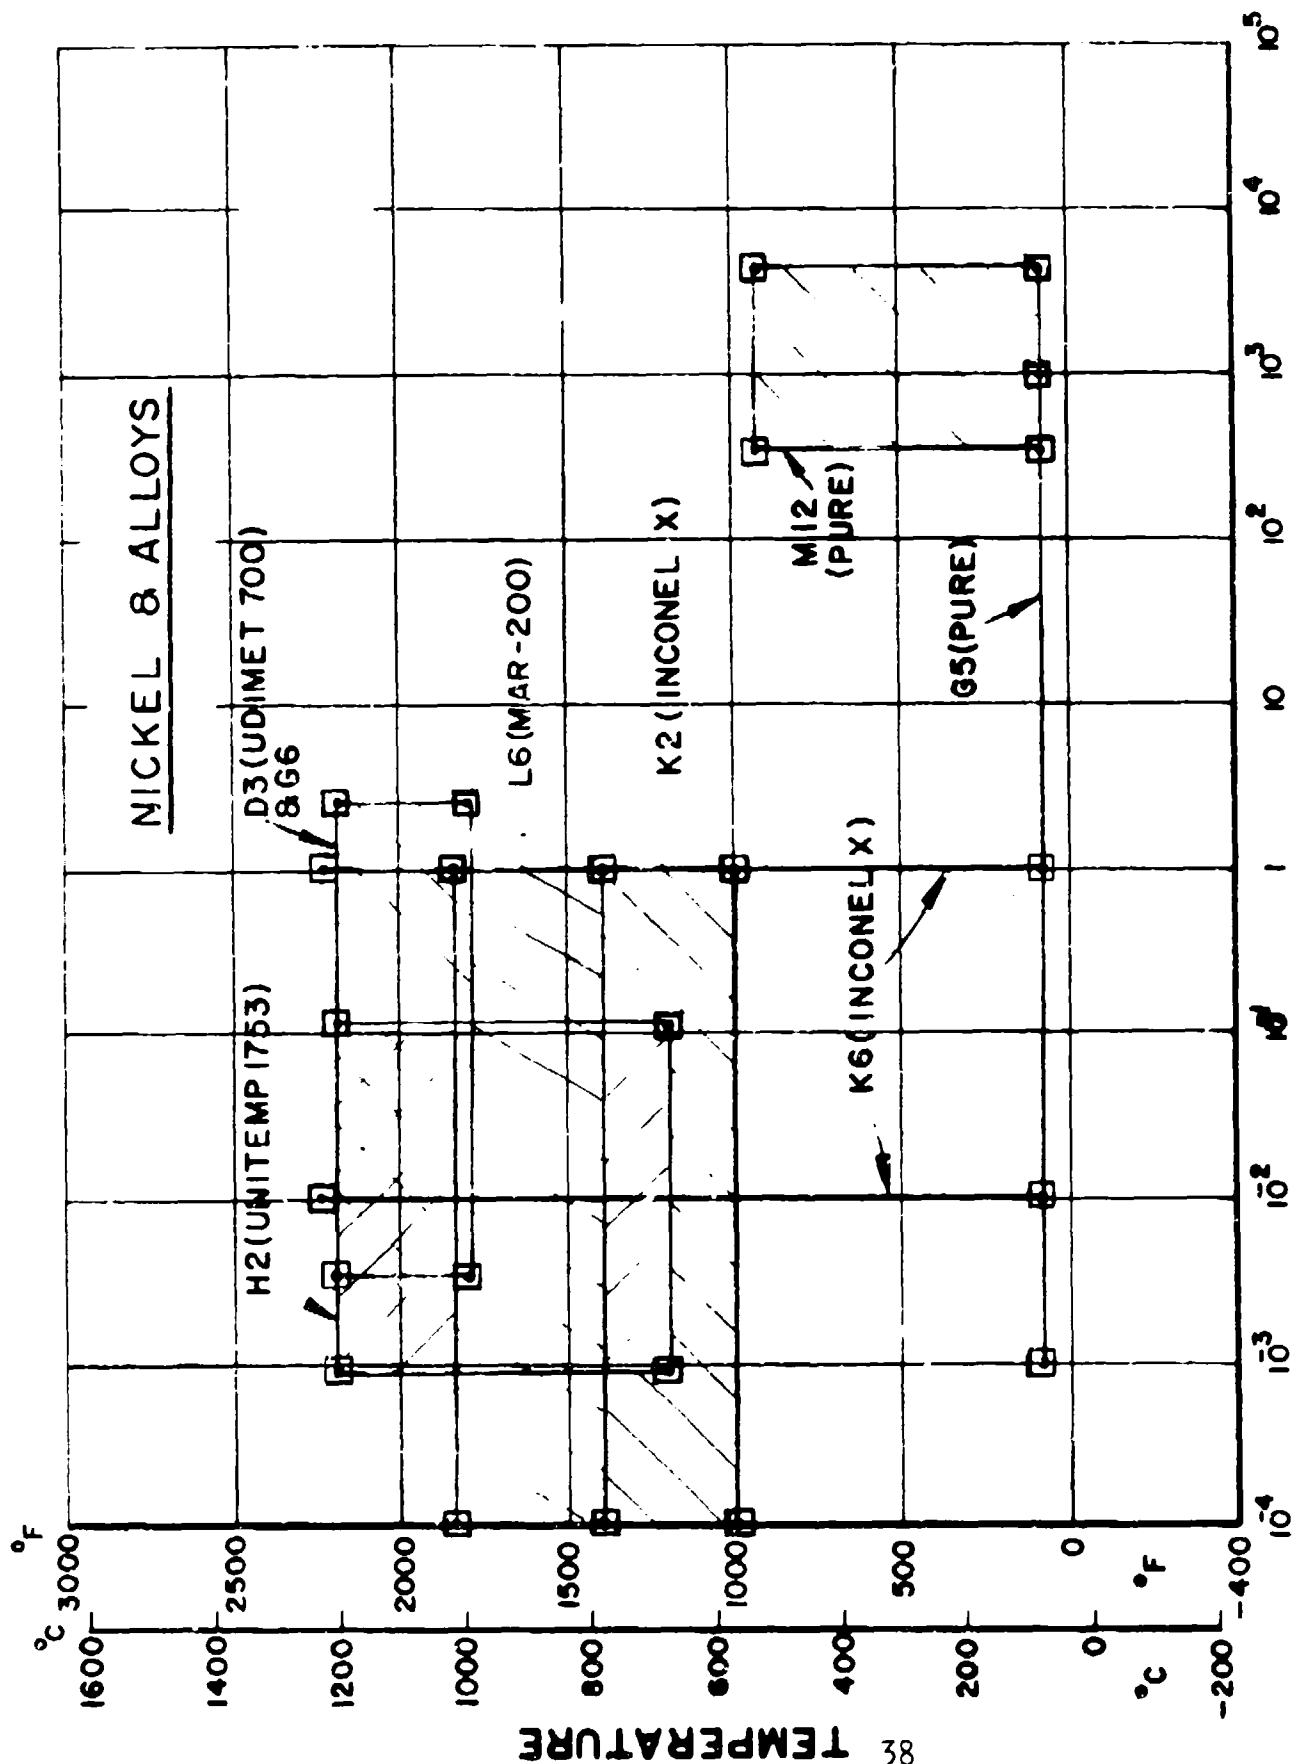

## REFRACTORY METALS

### Molybdenum

Three references give stress versus strain rate results for pure molybdenum. These are all in good agreement and show generally linear increases in strength with logarithmic strain rate over the range of  $10^{-4}$  to  $10^2 \text{ sec}^{-1}$ . The yield strength increases by about 100% over this range and the flow stress at various strains shows the same absolute increase. At temperatures above and below room temperature (200-600K) the yield stress-strain rate curves are essentially parallel to the room temperature curves. At very high temperatures (2000 to 4000F) only creep-rupture data are available. These show the same general trends as indicated above.

The molybdenum alloys studied include TZC, ZC-1 and ZC-2. These alloys show a peak in the strength-temperature curves at 2000F for the TZC and at 2700 F for the ZC alloys. This is attributed to dynamic strain aging and results in a negative rate sensitivity which, for the TZC alloy, extends from 900 F to 2100 F. At higher and lower temperatures the rate sensitivity is positive.

An important feature of molybdenum alloys is that they exhibit a very sharp ductile to brittle transition as the temperature decreases. At static strain rates, this transition temperature is usually just below room temperature. However, at higher strain rates this temperature may be shifted to a higher value which may be at, or slightly above, room temperature. This offers a very severe design limitation for these materials.

### Tungsten and Tantalum

The behavior of these two materials is somewhat similar. Both exhibit a yield point instability phenomenon. The upper yield stress is highly rate sensitive while the peak flow stress is much less rate sensitive. At high strain rates the upper yield stress may be significantly higher than the peak flow stress.

At elevated temperatures to 900 F the behavior is similar to that at room temperature for the two tungsten alloys studied. In pure tantalum a temperature of 500F essentially eliminates the upper yield point and decreases the rate sensitivity.

### Niobium (Columbium)


The flow stress and the yield stress of this material at room temperature show a slight rate sensitivity at strain rates below  $10^{-2}$   $\text{sec}^{-1}$  and a strong rate sensitivity at higher rates with a 60% increase in strength at  $100 \text{ sec}^{-1}$ . At lower temperatures the relative rate sensitivity remains about the same as at room temperature. At higher temperatures up to about 500F the rate sensitivity decrease significantly. No data are available for higher temperatures or for niobium based alloys.



TEMPERATURE °C 3000 1600 1400 1200 1000 800 600 400 200 0 -200 °F 3600 2400 2000 1600 1200 800 400 0 -200

TO 4000 F

3600 F

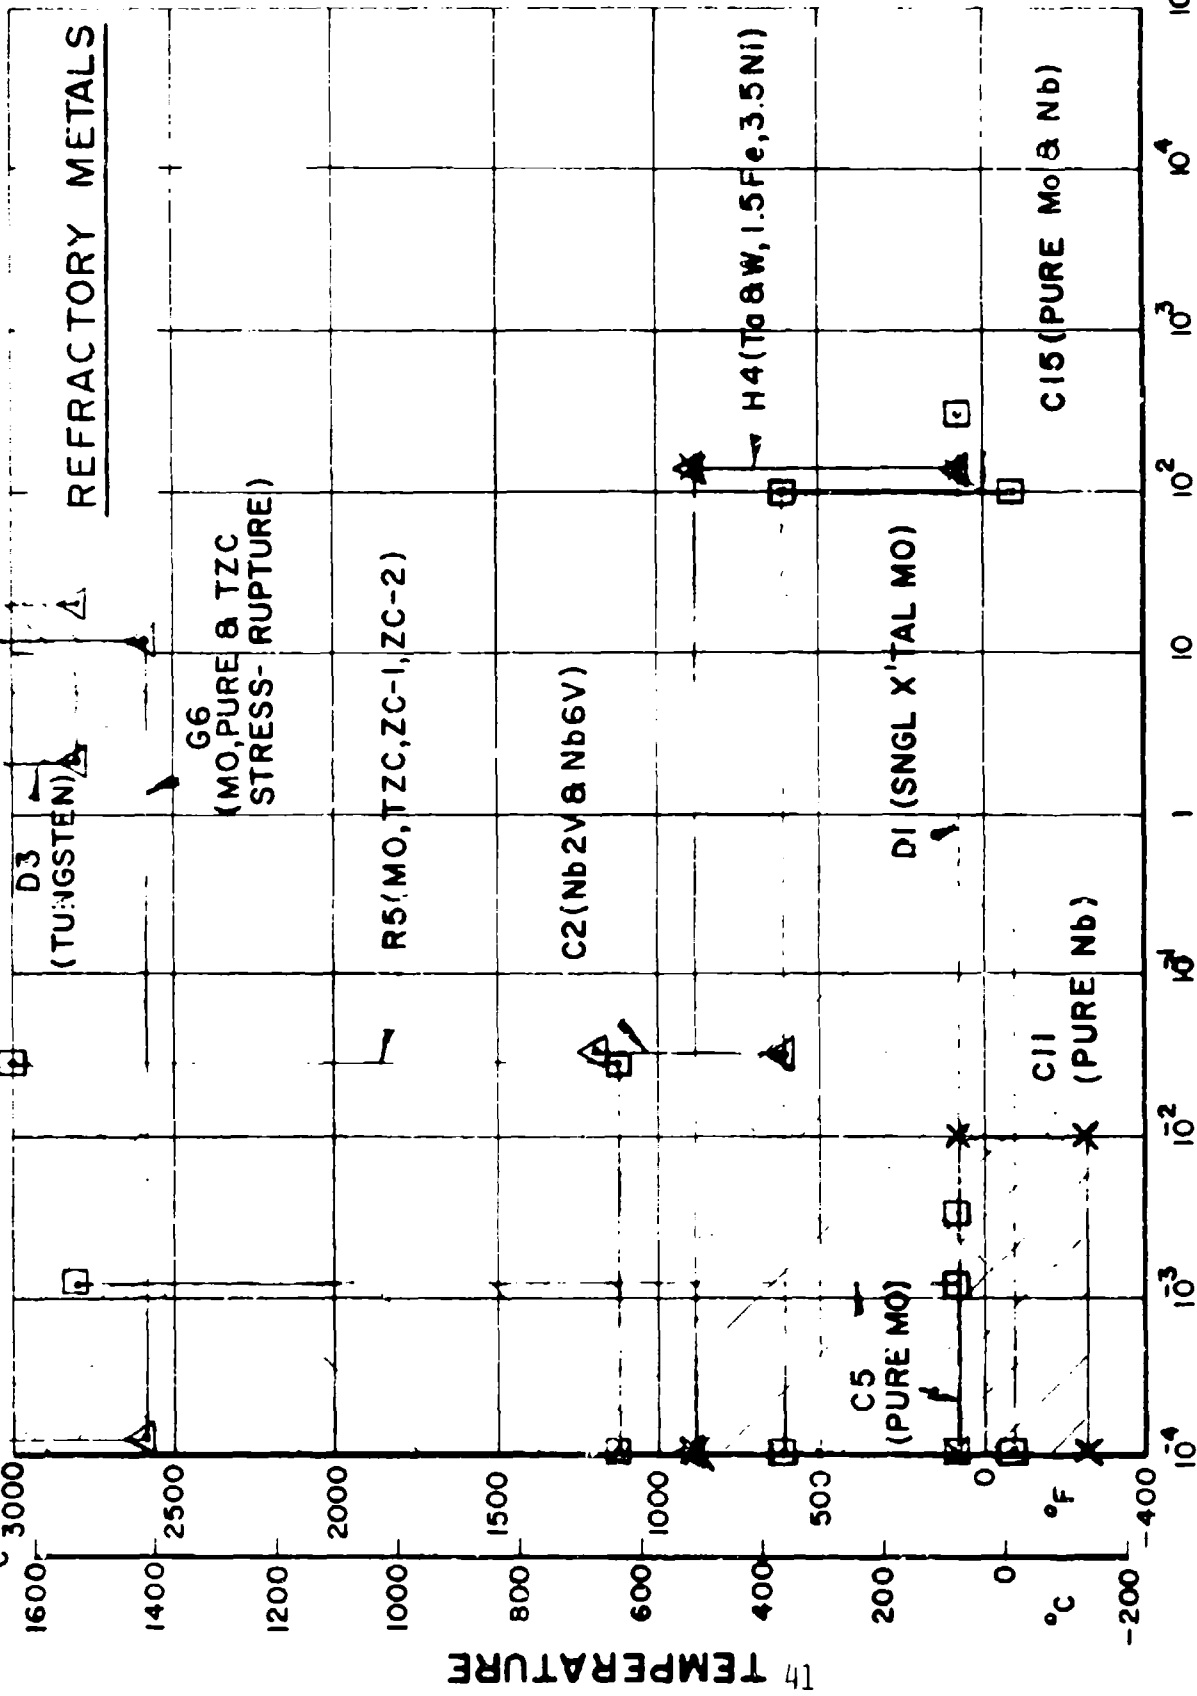

## OTHER METALS AND ALLOYS

### Uranium

Data are available for uranium alloys containing 10% Mo and 8% Mo, 0.5% Ti. Both show similar results at room temperature with an approximately linear increase in strength with logarithmic strain rates. The strength increases by 40 to 50 ksi with an increase in strain rate from  $10^{-3}$  to  $10^3 \text{ sec}^{-1}$ . The strength-strain rate curves at temperatures from -65F to 600F are essentially parallel to the room temperature curves.

### Thorium

Thorium also shows a linear increase in strength with logarithmic strain rate up to a rate of about  $10 \text{ sec}^{-1}$ . Above this the rate sensitivity appears to decrease slightly. The flow stress at various values of plastic strain show similar rate sensitivity.


### Cobalt Base Alloy (Stellite)

Results are available for annealed Stellite 25 sheet at strain rates of  $5 \times 10^{-5}$ ,  $10^{-2}$  and  $1.0 \text{ sec}^{-1}$  and at temperatures from room temperature to 2250F. Over this strain rate range the yield strength increases by about 20 ksi at temperatures from room temperature to 400F. At 1200 to 1600F an inverse rate sensitivity is seen and at higher temperatures a significant positive rate sensitivity is found.

## Beryllium

Two references give results for hot pressed beryllium. These are designated as 2043 and S-200E materials. Good agreement is found where the data overlaps. Only slight rate sensitivity was found at temperatures up to 1000F. Above this temperature the rate sensitivity increases with a strength increase from 6 ksi to 20 ksi at 1400F for an increase in strain rate from  $10^{-3}$  to  $1 \text{ sec}^{-1}$ . Extruded S-200E material also showed little rate sensitivity at room temperature but increased sensitivity in the range of temperatures from 600 to 1000F. A strength increase of 30 ksi was obtained for a strain rate increase from  $10^{-3}$  to  $10 \text{ sec}^{-1}$ .

# OTHER METALS & ALLOYS

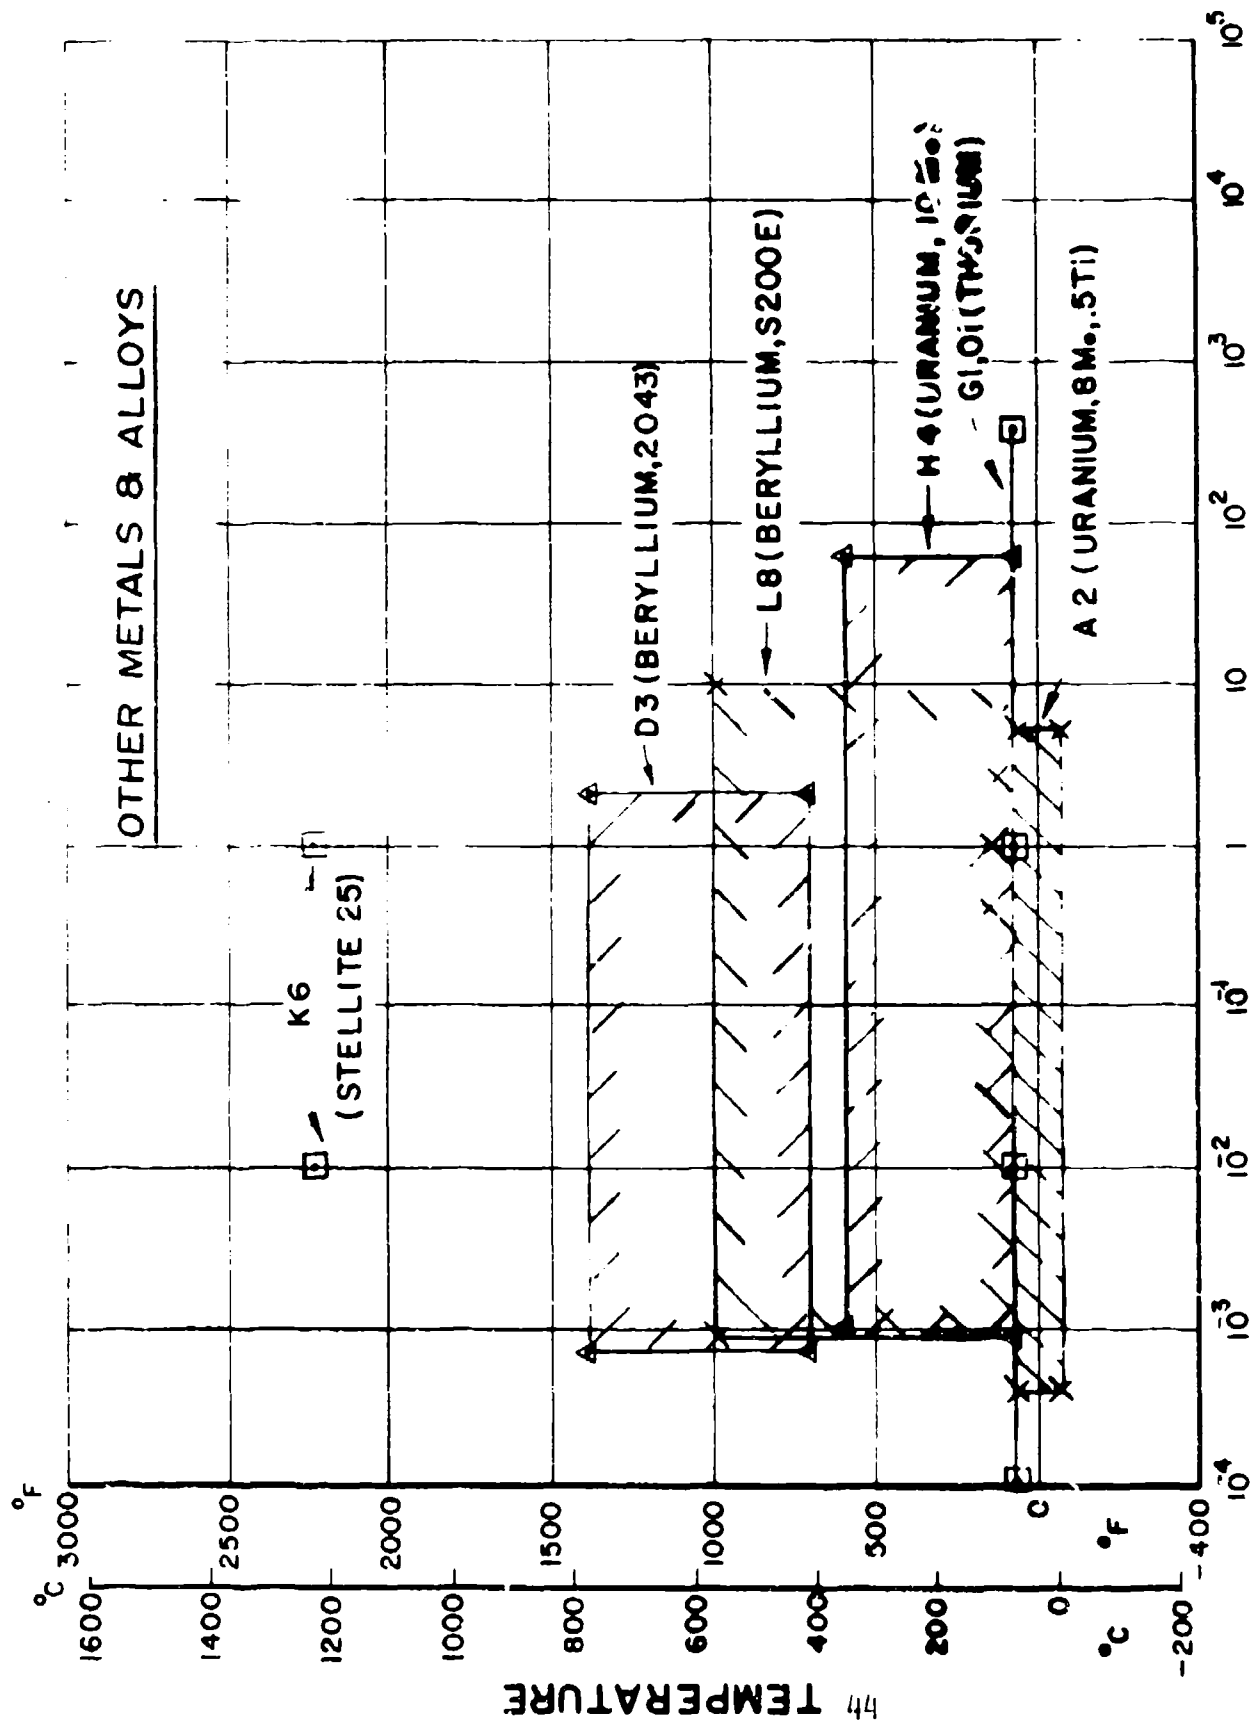

TEMPERATURE RANGE

## REFERENCES

- A1 Alder, J.F. & Phillips, V.A., "The Effect of Strain Rate and Temperature on the Resistance of Aluminum, Copper, and Steel to Compression", Inst. of Metals, V 83, pgs 80-86, 1954.
- A2 Anderson, "A Medium-Speed Tensile Testing Machine and Some Dynamic Data Produced Thereby", High Speed Testing, V IV, pgs 169-196, 1963.
- A3 Askloef, C.A., Nylander, A. & Persson, A.; "Literature Study on Metal Deformation and Strength Properties, Especially Under High Loading Rates", FOA-2-A-2497-44 (Stockholm), Sep 1967.
- A4 Austin, A. & Steidel, R.F.; "The Tensile Properties of Some Engineering Materials At High Rates of Strain", ASTM Proc V 59, pgs 1292-1308, 1959.
- B1 Bailey, J.A. & Singer, A.R.E., "Effect of Strain Rate and Temperature on the Resistance to Deformation of Aluminum, Two Aluminum Alloys, and Lead", J. Institute of Metals, V 92, pgs 404-408, 1963.
- B2 Bailey, J.A. "Some Strain-Rate Effects Observed During Deformation in Plane Compression", ASME, 67-MET-11, 1967.
- B3 Baker, W.E. & Yew, C.H.; "Strain-Rate Effects in Propagation of Torsional Plastic Waves", Univ of Texas Report, EMKL-RM-1006, June 1965.
- B4 Baucom, R.M., "Strain Rate Sensitivity of Three Titanium Alloy Sheet Materials After Prolonged Exposure at 550°F (561°K)", NASA-TN-D-4981, Jan 69.
- B5 Butcher, B.M. & Canon, J.R.; "Influence of Work-Hardening on the Dynamic Stress-Strain Curves of 4340 Steel", AIAA Jour, V 2, No. 12, 1964.
- C1 Cadle, H.H.; "High-Rate Loading: Effect on Mechanical Properties of Cr-Mo-V and 4340 Steel at Ambient Temperature", Springfield Armory SA-TR-18-1203, Oct 64.
- C2 Calhoun, C.D. & Weisinger, F.W.; "Tensile and Creep Properties of Niobium-Vanadium Alloys as Influenced by Strain Rate", KAPL (GE) Report 3145, Jun 66.
- C3 Campbell, J.D. & Ferguson, W.G.; "The Temperature and Strain-Rate Dependence of the Shear Strength of Mild Steel", Phil. Mag., Vol 21 No. 169, pgs 63-82, Jan 70.
- C4 Campbell, J.D. & Harding, J.; "Effect of Grain Size, Rate of Strain, and Neutron Irradiation on the Tensile Strength of Alpha Iron" AIME-Interscience 1961, pgs 51-76 Response of Met to HV Def.

- D3 Dhosi, J.M., Widmer, R. & Grant, N.J.; "High Temperature Deformation and Fracture Behavior of Metals under High Strain Rate Conditions", Contract NOW 63-0502c, Final Report, Oct 1964.
- D4 Desisto, T.S. & Driscoll, D.E.; "Effect of Strain Rate and Temperature on the True Stress-True Strain Properties of Commercially Pure Titanium", Hi Speed Testing, Interscience, V 1, pgs 97-105, Dec 58.
- D5 Duffy, J. Campbell, J.D. & Hawley, R.H.; "On the Use of a Torsional Split Hopkinson Bar to Study Rate Effects in 1100 - 0 Aluminum", Brown Univ Rept NSF-GK4242/1, Jan 70.
- D6 Duwez, P.E., Wood, D.S. & Clark, D.S.; "Dynamic Tests of the Tensile Properties of SAE 1020 Steels, Armco Iron and 17 ST Aluminum Alloy", National Defense Res Comm Armor & Ord Rept A-182, May 43.
- E1 Eleiche, A.M., "A Literature Survey of the Combined Effects of Strain Rate and temperature on the Mechanical Properties of Metals", Brown Univ AFMLTR-72-125, Sep 72.
- F1 Fenn, R.W. & Gusack, J.A. "Effect of Strain Rate and Temperature on the Strength of Magnesium Alloys", ASTM Proc. V 58, pgs 685-696, Jun 58.
- F2 Frantz, R.A. & Duffy, J. "The Dynamic Stress-Strain Behavior in Torsion of 1100-0 Aluminum Subjected to a Sharp Increase in Strain Rate", Brown U-DAHC04-70C-0035/1, Feb 71.
- G1 Gallman, R.A. & Oakes, R.E. "Compressive Strain-Rate Properties of Thorium", Union Carbide Report Y1707, Mar 70.
- G2 Garner, R.R. "Behavior of Yield and Ultimate Strengths of Steel Under Dynamic Loading", J. of Materials, V 5 No. 3, Sep 70.
- G3 Gondusky, J.M. & Duffy, J. "The Dynamic Stress-Strain Relation of Lead and its Dependence on Grain Structure", Brown U-NONR-562(20)/53, May 67.
- G4 Grant, N.J., Bridenbaugh, P. & Kane, R.; "Deformation and Fracture as a Function of Strain Rate at Hot Working Temperatures", Naval Air Systems Contract N00019-67C-0220, June 1967.
- G5 Green, S.J., Maiden, C.J., Babcock, S.G. & Schierloh, F.L.; "The High Strain Rate Behavior of Face Centered Cubic Metals", GM Tech Ctr MSL 69-36, Oct 69.
- G6 Grant, N.J., Bredenbaugh, P. & Kane, R.; "Deformation and Fracture as a Function of Strain Rate at Hot Working Temperatures", Mass Inst of Tech, Contract N00019-67C-0220, Final Report Sep 67.
- H1 Harding, J. & Campbell, J.D. "Effect of Strain Rate on Room Temperature Strength and Ductility of Five High-Strength Steels", Oxford U 1090-69-1R-4, Sep 69.

- C5 Carreker, R.P. & Guard, R.W.; "Tensile Deformation of Molybdenum as a Function of Temperature and Strain Rate", J. of Met AIME, pgs 178-184, Feb 56.
- C6 Chalupnik, J.D. & Ripperger, E.A.; "Dynamic Deformation of Metals under High Hydrostatic Pressure", 2nd Int Congress Experi Mech 1965.
- C7 Chiddister, J.L. & Malvern, L.E.; "Compression-impact Testing of Aluminum at Elevated Temperatures", Experimental Mechanics, V 3 No. 4, Apr 63.
- C8 Clark, D.S. and Wood, D.S.; "The Tensile Impact Properties of Some Metals and Alloys", Trans ASM, V 42, pgs 45-74, Feb 1949.
- C9 Clark, D.S. & Duwez, P.E.; "The Influence of Strain Rate on Some Tensile Properties of Steel", ASTM Proceedings, V 50, pgs 560-576, 1950.
- C10 Conn, A.F. & Thiruvengadam, A.; "Experimental Research on High Frequency Fatigue and Dynamic Tensile Tests at Elevated Temperatures", NASA-CR-72618, Jul 69.
- C11 Conrad, H. & Stone, G.A.; "The Effect of Temperature and Strain Rate on the Yield and Flow Stresses in Niobium", Aerospace Corp, ATN-64(9236)-6, Jan 64.
- C12 Cook, P.M.; "True Stress-Strain Curves for Steel in Compression at High Temperatures and Strain Rates, for Application to the Calculation of Load and Torque in Hot Rolling", Prop of Metals @Hi Rates of Strain, Inst of Mech Engr May 1957.
- C13 Cox, A.R. & Hettche, L.R.; "The Flow Strength Dependence on Temperature and Strain Rate in Low Carbon Iron Alloys", NRL Report No. 7283, Aug 71.
- C14 Christman, D.R., Isbell, Wm & Babcock, S.G.; "Measurements of Dynamic Properties of Materials", Vol. V, OFHC Copper, General Motors Tech Ctr, MSL70-23, Jul 71.
- C15 Campbell, J.D. & Briggs, T.L.; "The Effect of Strain Rate and Temperature on the Yield and Flow of Polycrystalline Niobium", Oxford Univ Report No. 1091, 1969.
- D1 Davidson, D.L., Lindholm, U.S. & Yeakley, L.M.; "The Deformation Behavior of High Purity Polycrystalline Iron and Single Crystal Molybdenum as a Function of Strain Rate at 300° K", ACTA Met V 14, pgs 703-710, Jun 66.
- D2 D'Antonio, C.R., Maciag, R.J., Mukherjee, K. & Fischer, G.J.; "The Effect of Strain Rate and Temperature on the Flow Stress of 7075 Aluminum", Trans AIME V242, pgs 2295-2297, Nov 1968.

- H2 Harpster, N.R., & Sye, J.H., "Some Effects of Temperature and Strain Rate on the Tensile Properties of Solution Treated Unitemp 1753 Bar Stock", Universal Cyclops 136, Jun 59.
- H3 Hoge, K.G., "Influence of Strain Rate on Mechanical Properties of 6061-T6 Aluminum under Uniaxial and Biaxial States of Stress", Exper Mech, Vol 6 No. 4, Apr 66.
- H4 Hoge, K.G., "The Effect of Strain Rate on Mechanical Properties of Some Widely Used Engineering Metals", U. of Calif, UCRL-14599, Dec 65.
- H5 Honeycutt, J.H., "Rapid Heating and Loading of 5052-H34 Aluminum Alloy Sheet", Redstone Ais Report No. RS-TR-69-2, Mar 69.
- H6 Hockenhuill, B.S., "Some Further Experiements in Fatigue Testing at 20 kHz", College of Aeronautics, COA Note-Mat-24 pg 16, Oct 68.
- H7 Hinesley, C.P. & Morris, J.G.; "The Effect of Structure on the Strain Rate Sensitivity of 3003 Ae-Mn Alloy", Mat'ls Sci & Engr. Vol 6 pg 48-54, 1970.
- I1 Iyer, K.R. "Effect of Strain Rate on the Mechanical Properties of Cr-MO-V Steel at Elevated Temperatures", Rock Island Ars Report No. SWERR-TR-72-6, Feb 72.
- K1 Karnes, C.H. "Strain-Rate Effects in Cold-Worked High-Purity Aluminum", U. of Texas Report on DA Proj No. 009925001, Dec 63.
- K2 Kattus, J.R. "The Effects of Strain Rate and Temperature on Metals", Metals Prog. Dec 61.
- K3 Kendall, D.P. & Davidson, T.E. "The Effect of Strain Rate on Yielding in High Strength Steels", ASME J Basic Eng, V 88, series D No. 1 pg 37-44, Mar 66.
- K4 Kendall, D.P. "The Effect of Strain Rate and Temperature on Yielding in Steels", ASME J Basic Eng V 94, Series D No. 1 pg 207-212, Mar 72.
- K5 Krafft, J.M. & Sullivan, A.M.; "On Effects of Carbon and Manganese Content and of Grain Size on Dynamic Strength Properties of Mild Steel", Trans ASM V 55, pgs 101-118, 1962.
- K6 Kattus, J.R. "Tensile Properties of Aircraft Structural Metals at Various Rates of Loading After Rapid Heating, Part II: WADC Tech Report No. 58440, May 59 and Dedman, Wheelahan & Kattus (same title) Part I, Nov 58.
- K7 Kendall, D.P. "The Effect of Loading Rate and Temperature on the Fracture Toughness of High-Strength Steels", ASTM Mat'ls Res & Stds, V 10, No. 2, 70.



- L1 Lindholm, U.S., "Dynamic Deformation of Metals", Behavior of Materials Under Dynamic Loads", ASME, 1965.
- L2 Lindholm, U.S. & Bessey, R.L.; "A Survey of Rate Dependent Strength Properties of Metals", AFML, TR69-119, April 1969.
- L3 Lindholm, U.S. & Yeakley, L.M., "Dynamic Deformation of Single and Polycrystalline Aluminum", J. Mech & Phys Solids, Vol 13, pgs 41-353, 1965.
- L4 Leslie, W.C. & Sober, R.J.; "The Strength of Ferrite and of Martensite as Functions of Composition, Temperature and Strain Rate", Trans ASM, Vol 60, pgs 459-484, 1967.
- L5 Leslie, W.C., Sober, R.J., Babcock, S.G. & Green, S.J.; "Plastic Flow in Binary Substitutional Alloys of BCC Iron-Effects of Strain Rate, Temperature and Alloy Content", Trans ASM, Vol 62, pgs 690-710, 1969.
- L6 Leverant, G.R., Gell, M. & Hopkins, S.W.; "The Effect of Strain Rate on the Flow Stress and Dislocation Behavior of a Precipitation-hardened Nickel-base Alloy", Mat'ls Sci & Engg V 8, pgs 125-133, 1971.
- L7 Lindholm, U.S., Yeakley, L.M. & Bessey, R.L.; "An Investigation of the Behavior of Materials Under High Rates of Deformation", AFML-TR-68-194, Jul 1968.
- L8 Lindholm, U.S. & Yeakley, L.M., "Effect of Strain Rate, Temperature and Multiaxial Stress on the Strength and Ductility of S200E Be and 6Al, 4VTi, AFML-TR-71-37, Mar 71.
- M1 MacDonald, R.J., Carlson, R.L. & Lankford, W.T.; "The Effects of Strain Rate and Temperature on the Stress-Strain Relations of Deep-Drawing Steel", Proc ASTM, Vol 56, pgs 704-720, 1956.
- M2 Maiden, C.J., "Some Investigations of the Dynamic Strength of Low Carbon Steels", CARDE Tech Memo AB-58, Mar 1960.
- M3 Maiden, C.J. & Green, S.J.; "Response of Materials and Structures to Suddenly Applied Stress Loads (Phase 1)", GM Interim Report No. TR65-69, Oct 65.
- M4 Maiden, C.J. & Green, S.J. "Compressive Strain-Rate Tests on Six Selected Materials at Strain Rates From  $10^{-3}$  to  $10^4$  In./In/Sec", ASME J. of Appl Mech, Sep 66.
- M5 Malvern, L.E. "Experimental Studies of Strain-Rate Effects and Plastic-Wave Propagation in Annealed Aluminum", Behavior of Mat'ls Under Dyn Load ASME Nov 65.
- M6 Manjoine, M.J. "Influence of Rate of Strain and Temperature on Yield Stresses of Mild Steel", J. of Appl Mech, Vol 11, pgs A211-218, 1944.

- M7 Marsh, K.J. & Campbell, J.D.; "The Effect of Strain Rate on the Post-Yield Flow of Mild Steel", J. Mech & Phys of Solids Vol 11, pgs 49-63 1963.
- M8 Moon, D.P. & Campbell, J.E.; "Effects of Moderately High Strain Rates on the Tensile Properties of Metals", DMIC Report AD 270-167.
- M9 Morris, J.G. "Dynamic Strain Aging in a Ti-Modified 316 Stainless Steel", Mat'ls Sci & Engr, Vol 7, pgs 296-301, 1971.
- M10 Morris, J.G. & Howard, H.K.; "Inverse Strain-Rate Effects in Aluminum Alloys", J. of Applied Physics, Vol 42, No. 8, Jul 71.
- M11 Morris, J.G., Skaggs, R.L., Howard, J.K. & Tidwell, J.T.; "The Effect of Strain Rate on the Deformational Instability of Aluminum Alloys" Mat Sci & Engr, Vol 4 pg 198-205, 1969.
- M12 Muller, T. "The Visco-Plastic Dynamic Behavior of Iron and Nickel at Elevated Temperatures", ACTA Metallurgica, Vol 19, pgs 691-699, Jul 71.
- N1 Nicholas, T. & Garey, G.F.; "Torsion Testing of Aluminum at High Rates of Strain", AFML-TR-69-172, Jul 69.
- N2 Nicholas, T. & Whitmire, J.N.; "The Effects of Strain-Rate and Strain-Rate History on the Mechanical Properties of Several Metals", AFML-TR-70-218, Aug 70.
- N3 Naybour, R.D. "Hardening During Deformation of An 18Cr/12Ni/Nb Austenitic Steel at 650° C.", ACTA Metallurgica, V 13, pgs 1197-1207, Nov 65.
- O1 Oakes, R.E. & Gallman, R.A.; "Tensile Strain-Rate Properties of Thorium", Union Carbide Corp, Y-1708, Feb 70.
- P1 Panda, J.F. & Abbe, E.H.; "Influence of Crystallographic and Metallographic Structures on Dynamic Behavior of Materials", Springfield Armory Report No. SA-TR18-1204, Nov 65.
- R1 Ripperger, E.A.; "Dynamic Plastic Behavior of Aluminum, Copper and Iron", Behavior of Mat'ls under Dyn Loads, ASME, pgs 62-80, 1965.
- R2 Roberts, J. "Relationships Between the Tensile Properties of Materials Tested at Low and High Rates of Strain", Explosives Research & Development Establishment, Report No. 6/R/61, Jun 61.
- R3 Rosen, A. & Bodner, S.R.; "The Influence of Strain Rate and Strain Ageing on the Flow Stress of Commercially-Pure Aluminum", Mech Phys Solids, V 15, pgs 47-62, 1967.

- R4 Russell, T.L., Wood, D.S. & Clark, D.S.; "The Influence of Grain Size on the Yield Phenomenon in Steel", ACTA Metallurgica, Vol 9, pgs 1054-1063, Dec 1961.
- R5 Raifo, P.L. "Dynamic Strain Aging in Carbide-Strengthened Molybdenum Alloys", Met Trans, Vol 1, pgs 835-841, Apr 70.
- R6 Rohde, R.W., Leslie, W.C. & Glenn, R.C., "The Dynamic Yield Behavior of Annealed and Cold-Worked Fe-0.17 Pct Ti Alloy", Met Trans, Vol 3, pgs 323-328, Jan 1972.
- S1 Santhanam, A.T., Ramachandran, V. & Reed-Hill, R.E.; "An Investigation of the Shape of the Titanium Stress Strain Curves After a Strain Rate Change", Met Trans Vol 1, pgs 2593-2598, Sep 70.
- S2 Schultz, A.B. "Dynamic Behavior of Some Metals and Non-Metals Under Tensile Impact", AFML-TR-70-59, May 1970.
- S3 Smith, J.E. "Tension Tests of Metals at Strain Rates up to 200 Sec<sup>-1</sup>", Mat'l's Research & Stds, Vol 3, pgs 703-718, 1963.
- S4 Smith, R.C. "Studies of the Effect of Dynamic Preloads on the Mechanical Properties of Steel", SESA Preprint, paper no. 612, 1960.
- S5 Stein, D.F. "The Effect of Carbon on the Strain-Rate Sensitivity of Iron Single Crystals", ACTA Met, Vol 14, pgs 99-104, Feb 66.
- S6 Steichen, J.M. & Paxton, M.M.; "Interim Report: Effect of Strain Rate on the Mechanical Properties of Austenitic Stainless Steels", Hanford Engr, Dev Lab, TME-71-56, May 1971.
- S7 Samanta, S.K. "On Relating the Flow Stress of Aluminum and Copper to Strain, Strain-Rate and Temperature", Int. J. Mech Sci, Vol 11, pgs 433-453, 1969.
- T1 Trozera, T.A., Sherby, O.D & Dorn, J.E.; "Effect of Strain Rate and Temperature on the Plastic Deformation of High Purity Aluminum", Trans ASM Vol 49, pgs 173-188, 1956.
- W1 Winlock, J. "The Influence of the Rate of Deformation on the Tensile Properties of Some Plain Carbon Sheet Steels", Trans AIME, Journal of Metals, pgs 797-803, Jun 53.
- W2 Wood, D.S. & Clark, D.S.; "The Influence of Temperature Upon the Time Delay for Yielding in Annealed Mild Steel", Trans ASM, Vol 43, pgs 571-586 1950.
- W3 Work, C.E. & Dolan, T.J.; "The Influence of Strain Rate and Temperature on the Strength and Ductility of Mild Steel in Torsion", ASTM Proc V 53, pgs 611-626, 1953.

- Y1 Yen, C.C.S. & Yew, C.H.; "Dynamic Shear Stress-Strain-Strain Rate Relations of Iron", J. Of Mat'ls, JMLSA, V 4, No. 2, pgs 324-337, Jun 69.
- Z1 Zener, C. & Hollomon, J.H.; "Effect of Strain Rate Upon Plastic Flow of Steel", J. of Applied Physics, V 15, pgs 22-32, Jan 44.